

NANO EXPRESS

Open Access

Controlling exchange bias in Fe₃O₄/FeO composite particles prepared by pulsed laser irradiation

Zaneta Swiatkowska-Warkocka*, Kenji Kawaguchi, Hongqiang Wang, Yukiko Katou, Naoto Koshizaki

Abstract

Spherical iron oxide nanocomposite particles composed of magnetite and wustite have been successfully synthesized using a novel method of pulsed laser irradiation in ethyl acetate. Both the size and the composition of nanocomposite particles are controlled by laser irradiation condition. Through tuning the laser fluence, the Fe₃O₄/FeO phase ratio can be precisely controlled, and the magnetic properties of final products can also be regulated. This work presents a successful example of the fabrication of ferro (ferri) (FM)/antiferromagnetic (AFM) systems with high chemical stability. The results show this novel simple method as widely extendable to various FM/AFM nanocomposite systems.

Introduction

Magnetic nanoparticles and hybrid magnetic nanostructures are of growing interest because of their technological applications in magnetic recording media, sensitive magnetic sensors and various biomedical applications such as drug delivery system, hyperthermia or magnetic resonance imaging [1]. In order to fulfil the requirements of many of these applications, an accurate control over the coercivity is strongly required.

Exchange bias coupling at the ferro (ferri) (FM)/antiferromagnetic (AFM) interface has attracted considerable attention due to their applications in permanent magnet applications and high density recording media [2,3]. The exchange bias effect is manifested by the shifting and broadening of a magnetic hysteresis loop of a sample cooled under an applied field [1,4,5]. Although the intrinsic origin of exchange bias effect is not yet understood fully, it is generally accepted that the interface exchange coupling between FM and AFM is the origin of the exchange bias [6].

Exchange bias has been extensively studied in bilayer and multilayer thin films [7,8], nanoparticles with core/shell structure [9-11] and particles dispersed in matrix [12]. However, to date, the report about how to control

the exchange bias by changing the FM/AFM ratio is seldom.

So far, various experimental methods have been used to produce FM/AFM heterostructure particles, e.g. chemical and thermal decomposition [10,13,14], ball milling method [11], gas condensation and chemical vapour deposition [15,16]. However, decomposition methods need the chemicals which often cannot be removed and remain as residual molecules on particle surfaces. Gas-phase methods require expensive and large-scale vacuum equipments. Such methods are generally effective for preparing particles with a narrow size distribution. However, most of these approaches are limited to synthesizing particles with a diameter smaller than 30 nm. Additionally, most of mentioned methods lead to the sintering of two phases and the poor quality of the interface. This has been attributed to the weak interfacial interaction between the FM and AFM phases in particles and results in a weak exchange bias. Therefore, the development of new synthetic techniques for FM/AFM particles with high exchange bias is still a target of current research.

In this study, we demonstrate a novel method for preparing submicrometer iron oxide nanocomposite spherical particles by pulsed laser irradiation in liquid (PLIL). In contrast to the pulsed laser ablation in liquid using a focused laser beam, which has been widely studied, PLIL irradiating source particles dispersed in liquid with

* Correspondence: zaneta.swiatkowska@aist.go.jp
Nanosystem Research Institute, National Institute of Advanced Industrial Science and Technology (AIST), 1-1-1 Higashi, Tsukuba, 305-8565 Ibaraki, Japan

an unfocused laser light which gives relatively mild reaction conditions [17,18]. The present study demonstrates the easy control of size and composition of submicrometer spherical iron oxide particles by PLIL. Furthermore, we report the structural effect and the exchange bias effect in $\text{Fe}_3\text{O}_4/\text{FeO}$ composites by PLIL method. Varying the phase ratio of magnetite and wustite, we can control the coercivity and exchange bias effect.

Experimental

The magnetite nanoparticles were prepared by conventional co-precipitation from FeCl_2 and FeCl_3 at high values of pH. Iron salts were dissolved in water with a magnetic stirrer for 1 h. The pH value was increased by adding NaOH. The colour of the solution turned to black immediately, inducting magnetite formation. Magnetite particles were removed from the solution by using permanent magnet and were washed several times with deionized water. Finally, the magnetite nanoparticles were dispersed in ethyl acetate and transferred to a sealed cell with quartz window to introduce laser light. The magnetite nanoparticles were stirred and irradiated for 1 h with the third harmonic (355 nm) of an Nd:YAG (yttrium aluminium garnet) laser operated at 30 Hz without focusing. Laser fluence varied from 33 to 177 mJ/pulse cm^2 . No evaporation of solvents was observed during irradiation.

The formed iron oxide phases and composition were determined by a powder X-ray diffractometer (XRD) (Rigaku Ultima IV, Rigaku Corporation, Akishima, Tokyo, Japan) with $\text{CuK}\alpha$ radiation. The morphology of the obtained particles was observed by a field emission scanning electron microscope (FE-SEM) (Hitachi S4800, Hitachi High Technologies Japan Inc., Tokyo, Japan) and a transmission electron microscope (TEM) (JEOL JEM 2010, Tokyo, Japan). Average particle size was determined by measuring the diameters of 200 particles from SEM images. The size of spherical particles was simply defined from the diameter. Calculation of size of non-spherical particles was based on replacing a given particle with a sphere that has the same volume as a given particle. The chemical states of elements in the samples were confirmed by an X-ray photoelectron spectrometer (XPS) (PHI, Versa Probe, ULVAC-PHI, Inc., Chigasaki, Kanagawa, Japan). A highly sensitive superconducting quantum interference device (Quantum Design, MPMS, San Diego, CA, USA) magnetometer was employed to measure the magnetic properties of nanocomposite particles. Hysteresis measurements were recorded for dried samples of nanoparticles in a gelatin capsule. Hysteresis loops were obtained by using maximum applied field up to 50 kOe at 5 and 300 K. The exchange bias properties of samples were investigated by measuring field cooled (FC) hysteresis loops in the

temperature range 5-300 K. In the FC procedure, the sample was cooled down from the initial temperature of 300 K to the measuring temperature T , under an applied field 50 kOe. Once T was reached, the field was set to 50 kOe and the measurement of the loop started.

Results and discussion


Fabrication and structural investigation of $\text{Fe}_3\text{O}_4/\text{FeO}$ system obtained by PLIL method

The size and shape of the particles obtained by laser irradiation in ethyl acetate were examined by FE-SEM (Figure 1, left). The average diameter of raw magnetite nanoparticles in the aggregates (Figure 1 before irradiation) is estimated to be 6 nm. Figure 1 indicates that spherical particles with smooth surfaces were formed after laser irradiation. Their spherical shape clearly indicates melt formation during the process, which suggests that the temperature of the particles is transiently increased over the melting point of iron oxide. A fluence increases from 33 to 177 mJ/pulse cm^2 and shows a systematic increase in the particle size from 150 to 460 nm (Figures 1 and 2).


The relationship between particle size and fluence is simply explained by the thermal energy absorbed of laser light. The absorption cross section of particles with diameters larger than the irradiation laser wavelength is considered the same as the geometrical cross section. The minimum energy to melt a particle is proportional to the particle volume ($\propto d^3$), while the absorption energy is proportional to the particle's cross section ($\propto d^2$). Thus, the minimum fluence to melt a particle is proportional to the diameter $d = d^3/d^2$. The relationship, however, is not so simple for particles with a diameter equal to or less than laser wavelength because of the complex dependence of the cross section on particle size [18,19].

TEM analyses provided more detailed structural information on the submicrometer spheres (Figure 1, right). Some of the particles formed at 33-66 mJ/pulse cm^2 had hollow structures. In contrast, smaller particles ranging from 5 to 60 nm were embedded in the larger spherical particles at a fluence exceeding 100 mJ/pulse cm^2 . In the intermediate fluence range of 66-100 mJ/pulse cm^2 , particles with a merged structure of two primary particles were observed.

X-ray diffraction patterns of particles before and after laser irradiation (Figure 3) revealed a gradual phase transformation from magnetite (Fe_3O_4) to wustite (FeO) with fluence increase. Starting raw nanoparticles were confirmed to be a pure magnetite phase. The sample after irradiation at 33 mJ/pulse cm^2 remained pure magnetite without chemical change, though the crystalline size increased judging from the reduced width and increased intensity of the reflections. Small wustite reflections of

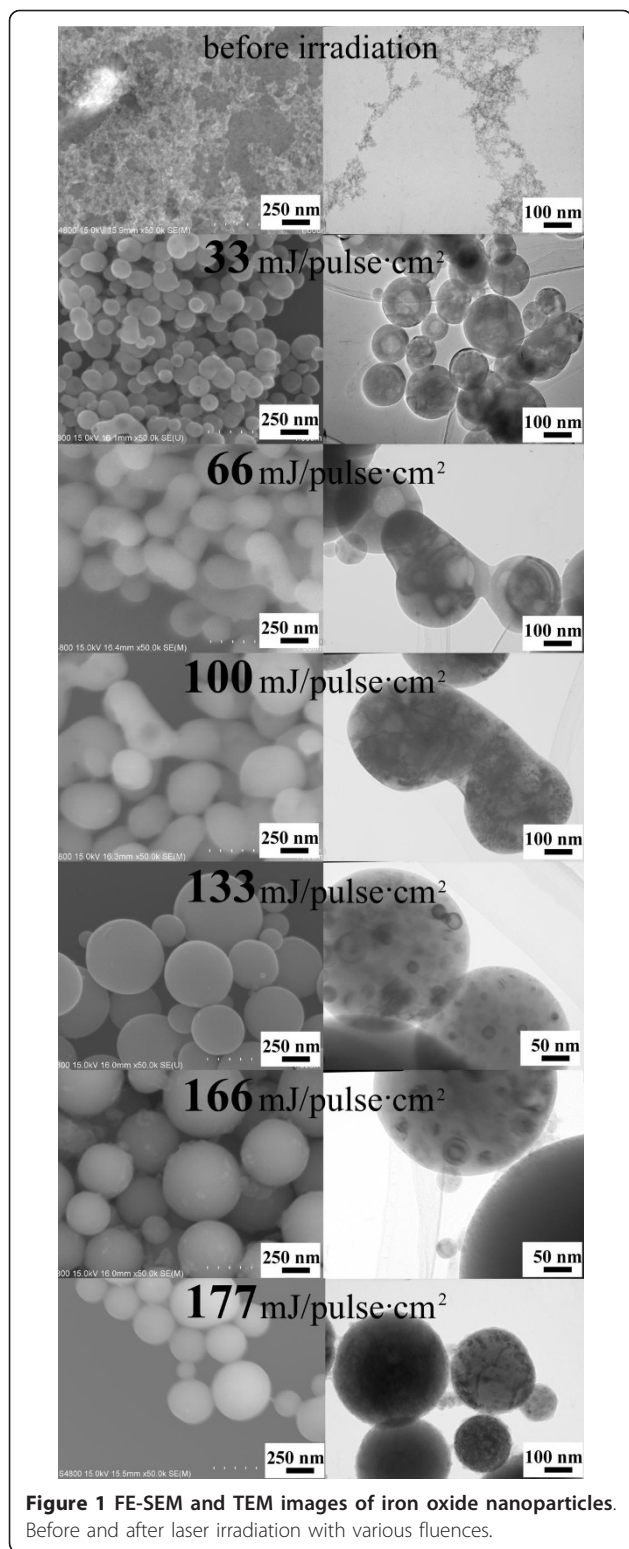

(111) at 36.1 and (200) at 42.0 appears as shoulders of magnetite (222) at 37.1 and (400) at 43.1, respectively in the 66-mJ/pulse cm^2 result in Figure 3. Those wustite reflections grew and magnetite ones decreased with the

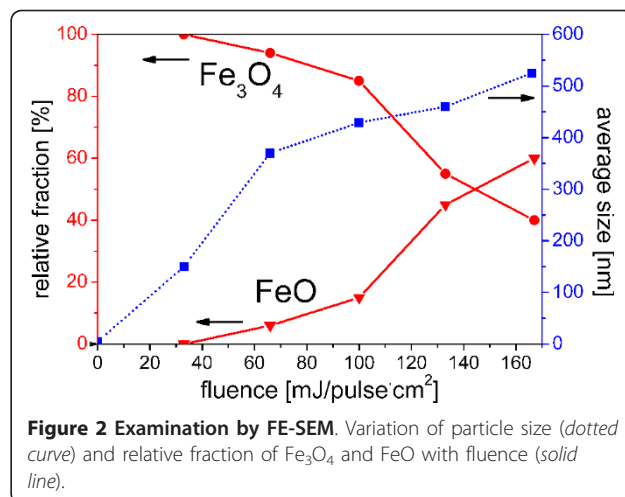


irradiation fluence increase. Volume fractions of Fe_3O_4 / FeO , calculated by ratio of highest intensity peaks from XRD data, are summarized in Figure 2.

Further information about the iron oxide formation during laser irradiation can be gained by analyzing XPS data. For the sake of simplicity, just the XPS Fe 2p depth profile of sample obtained after irradiation with fluence 177 mJ/pulse cm^2 is shown as being representative of the behaviour of all composite particles (Figure 4). All spectra for pre-sputtering and post-sputtering shows peaks positioned around 711 and 724 eV, which are typical core level spectra of Fe_3O_4 and around 710 and 723 eV, which are characteristic for Fe^{2+} ions in FeO [20]. These results are qualitatively consistent to the XRD measurements. On the basis of TEM and XPS results, we can suppose that composite particles obtained by pulsed laser irradiation reveal aggregated structures.

Morphology and composition of the particles obtained by laser irradiation suggest that Fe_3O_4 nanoparticles are melted to form a large spherical shape and reduced to form FeO phase. Temperature to melt iron oxide nanoparticles definitely induces the decomposition of surrounding ethyl acetate and possibly leads to the reduction of magnetite to wustite. Thermodynamic calculation was performed to investigate the possible thermal decomposition reaction of ethyl acetate and probable reducing reaction of magnetite. Gibbs free energy calculation of possible thermal decomposition reaction suggests that ethyl acetate can be thermodynamically decomposed at 1,600°C (the melting point of bulk magnetite) to methane, ethylene, carbon monoxide or hydrogen, and that these gases can reduce Fe_3O_4 to FeO .


The magnetite nanoparticles dispersed in ethyl acetate melt and formed spherical hollow particles by laser irradiation at low fluence. The formation of submicrometer hollow particles at low fluence may be related to the

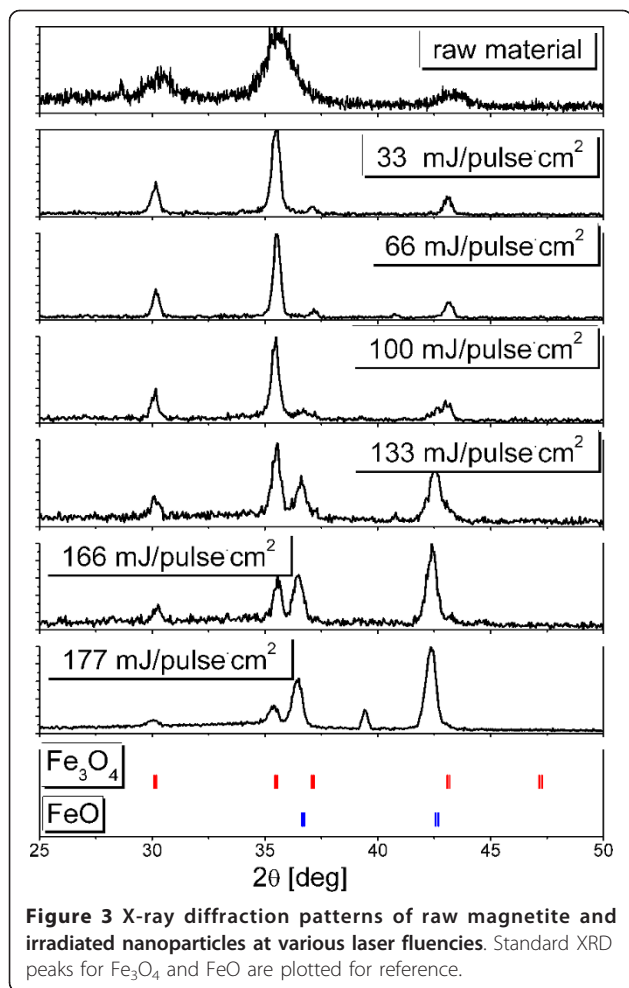

confining process of bubbles by melted droplets. Such bubbles may result from ultrasonic stirring during irradiation. With laser fluence increase, the reducing reaction with the decomposed gases becomes significant. Partial surface melting of particles causes coalescence with close neighbours (in the intermediate fluence range) and/or formation of spherical composite particles (in the high fluence range), together with the reducing reaction by decomposed gas from ethyl acetate. Thus, a hundred nanometer-sized particles composed of magnetite and wustite nanoparticles grow with increased fluence.

Magnetic properties of $\text{Fe}_3\text{O}_4/\text{FeO}$ system with different Fe_3O_4 to FeO phase ratios

In order to investigate the impact of different phase ratio of magnetite and wustite on the magnetic properties of the final $\text{Fe}_3\text{O}_4/\text{FeO}$ composite, the Fe_3O_4 nanoparticles dispersed in ethyl acetate were irradiated with the fluence of 133, 166 and 177 mJ/pulse cm^2 for 0.5, 1 and 2 h. The obtained particles are spherical with FeO volume fraction that varies from 20% to 85%. All

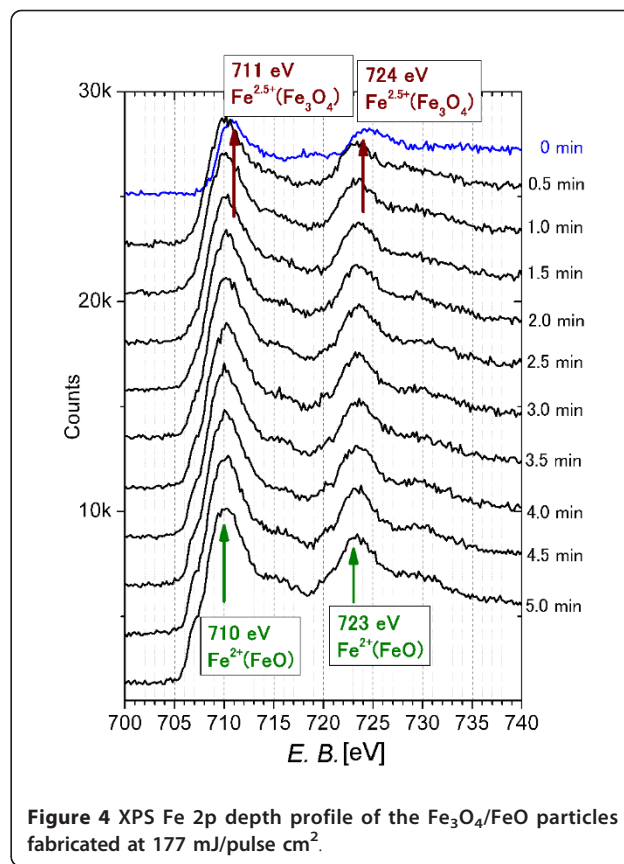

particles have similar structures to those presented in Figure 1 with the fluence of $133 \text{ mJ/pulse cm}^2$ or larger.

Exchange coupling at the FM/AFM interface of the $\text{Fe}_3\text{O}_4/\text{FeO}$ system is investigated by the zero field cooled (ZFC) and field cooled (FC) measurements of $M(H)$. Figure 5 illustrates the FC ($H_{\text{FC}} = 50 \text{ kOe}$) and ZFC hysteresis loops at 5 K for a cycling field of $\pm 50 \text{ kOe}$ of sample with 75% of wustite fraction (the ZFC and field cooled (FC) measurements of $M(H)$ curves for particles with 20%, 45%, 60% and 85% of FeO are presented in supporting information on Figure S1 in Additional file 1). The interesting feature in the $M(H)$ curves is that both the ZFC and FC loops remain open even in the 50 kOe field, known as the high field irreversibility, which could be interpreted as being due to the existence of the spin glass-like (SGL) phase [21,22]. According to the figure, this system exhibits the properties of exchange bias system, with a horizontal shift along the field axis of the FC hysteresis loop with respect to the ZFC hysteresis loop. The loop shift is defined as an exchange bias field $H_{\text{exch}} = |(H^+ + H^-)/2|$, where H^+ and H^- are positive and negative coercive fields. The FC hysteresis loop is shifted with an exchange bias field of 1,960 Oe. The coercivity field given by $H_c = (H^+ - H^-)/2$ is also obtained for both the ZFC case with the value of 514 Oe and a

considerably higher value of 1950 Oe for FC cases. The large coercivity and exchange bias indicates a strong magnetic interaction through the interface between magnetite and wustite. Additionally, a slight positive vertical shift along the magnetization axis is presented. In FM/AFM systems, vertical shifts are generally related to pinned uncompensated spins that exhibit either FM or AFM coupling at the interface [23]. The positive vertical shift in Figure 5 indicates a dominant FM coupling between the pinned uncompensated spins and the FM magnetization.

To reveal the effect of the phase ratio of FM and AFM phase on the exchange bias of FM/AFM composites, H_c and H_{exch} as a function of FeO phase ratio in Fe_3O_4/FeO particles was investigated. Figure 6 shows the variation of H_c (after ZFC) and H_{exch} (after FC in 50 kOe) with the increase FeO fraction in particles at 5 K. It is clear that H_c increases with the increasing FeO fraction, while H_{exch} firstly increases and then reaches a maximum of 1,960 Oe for 75% of wustite fraction. Further increase of FeO concentration leads to the decrease of H_{exch} . With increasing FeO concentration, the AFM phase can supply enough force to pin the uncompensated spin in FM phase which leads to a much stronger exchange interaction and further increase in H_{exch} . With a further increase in FeO concentration (> 75%), the balance between FM and AFM is destroyed, and H_{exch} do not increase continuously with increasing FeO concentration. In this case, 75% is a critical concentration of AF phase in Fe_3O_4/FeO composites. This result can confirm granular structure of obtained particles. With increasing FeO phase the effective interface area increases affecting exchange bias. AFM is too high for 75% of FeO concentration, and the effective interface


area rapidly decreases entailing the exchange bias decrease


In order to explore the origin of H_{exch} , the temperature dependence of H_{exch} obtained from magnetic hysteresis loops for the samples with 75% of FeO were also studied. The sample was first cooled down from 300 K to the measuring temperature under a magnetic field of 50 kOe, and then the loop was measured. This process was repeated for every measuring temperature. As presented in Figure 7, H_{exch} decreases with the temperature increase and appears to vanish at about 190 K. This blocking temperature is equal to the Neel temperature (T_N) of FeO (for FeO $T_N = 198$ K [24]). At a higher temperature, the coupling between FM and AFM regions is weakened by thermal disturbance. As the temperature decreases, the exchange interaction between the above two types of regions becomes stronger, resulting in the loop shift which becomes more prominent at a lower temperature. However, coercivity H_c does not decrease to zero and its value approaches to the intrinsic H_c of particles without exchange bias.

Thus, the observed exchange bias effect can be explored on the exchange coupling between the interfacial FM phase and AFM (or SGL) phase, and AFM can play an important role in pinning the uncompensated interfacial moments.

Conclusions


In conclusion, the pulsed laser irradiation technique was demonstrated to be a simple method for preparing sub-micrometer iron oxide heterostructure spherical particles. Size and composition of obtained particles can be tuned in a controllable manner by only laser fluence. Additionally, obtained particles exhibit interesting

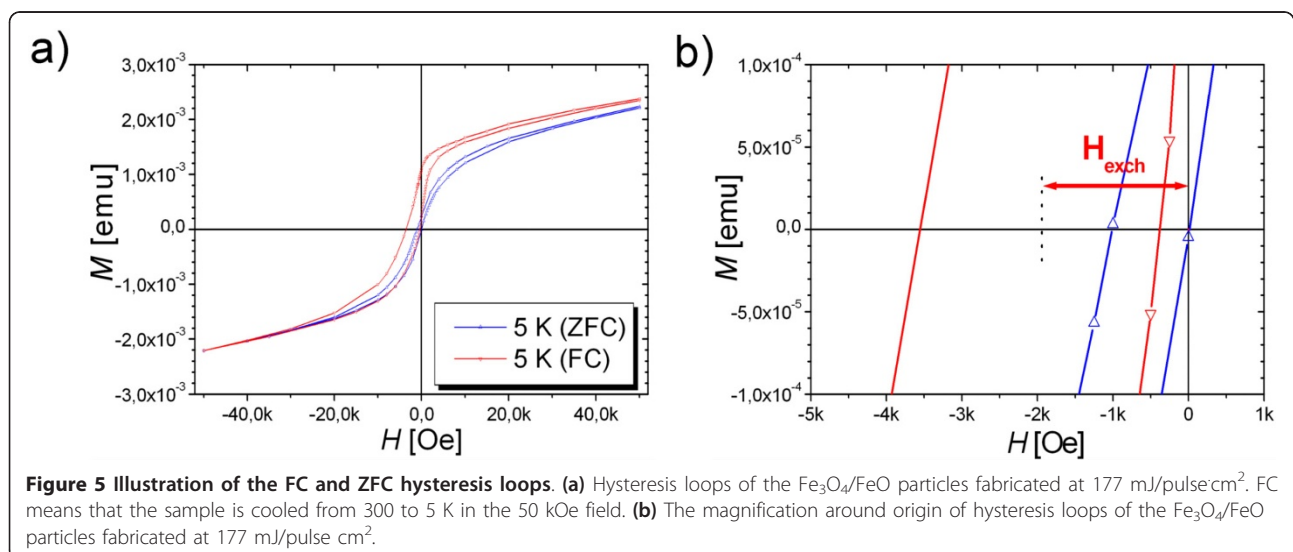

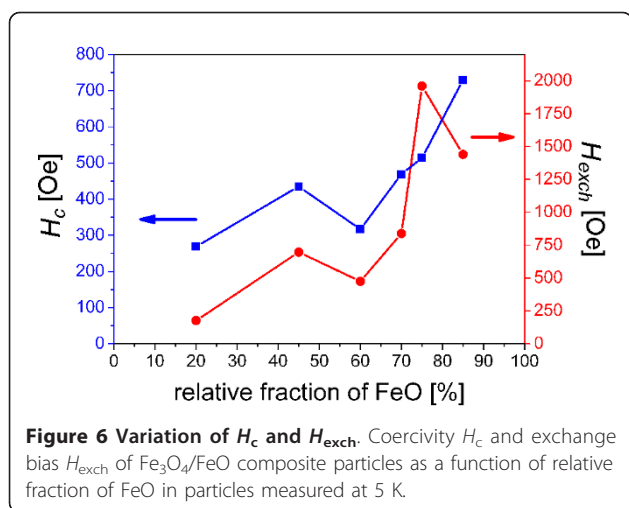

magnetic properties, especially exchange bias interaction at the ferrimagnet-antiferromagnet interface. For 75% of AFM concentration, the H_{exch} can reach the maximum value 1,960 Oe, at 5 K after field cooling. The reason is that the FM and AFM phase reach to the balance; the value of pinning force of AFM phase, which can play a significant role in pinning the uncompensated interfacial moments, is maximum. H_{exch} decreases with increasing temperature and approach zero at 190 K. The exchange bias originates from the exchange coupling between the interfacial FM phase and AFM phase. Although generally core/shell structures have been considered to explain a large exchange bias field, we have developed a new type of nanocomposite system with a large exchange bias field composed of ferrimagnetic Fe_3O_4 and antiferromagnetic FeO by pulsed laser irradiation of colloidal nanoparticles.

In contrast with common chemical methods, pulsed laser irradiation in liquid is very simple, low-cost, and contamination-free. Hence, we believe that our method

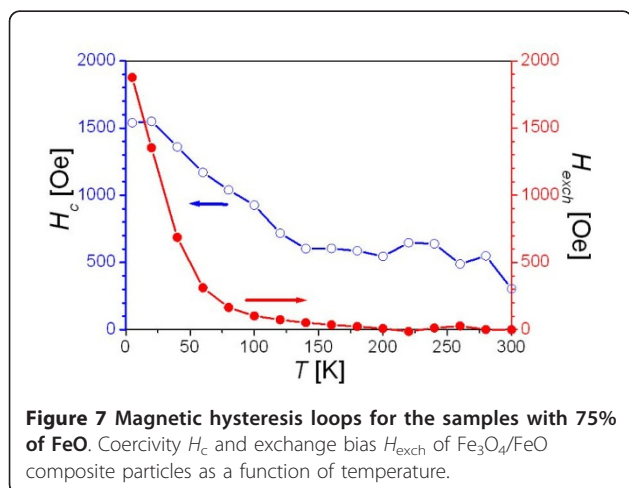

makes it possible to synthesize magnetic heterostructure particles with controllable size, composition and magnetic properties.

Additional material

Additional file 1: supporting information. Fig. S1 Magnetization vs. field loop measured at 5 K under ZFC and FC conditions $\text{Fe}_3\text{O}_4/\text{FeO}$ composite particles with different fraction of FeO.

Acknowledgements

This work was supported by KAKENHI 2008734, and the magnetization measurements were conducted at the Nano-Processing Facility, supported by IBEC Innovation Platform, AIST.

Authors' contributions

ZS-W conducted most of the experiments and performed data analysis. KK supported the magnetic property measurement and contributed the data interpretation. HW supported to construct the formation mechanism by providing relating data of similar systems. YK helped the most of operation and data interpretation of analytical equipments used. NK conceived basic idea of this technique and supported the organization of this paper.

Competing interests

The authors declare that they have no competing interests.

Received: 10 September 2010 Accepted: 16 March 2011

Published: 16 March 2011

References

- Nogues J, Sort J, Langlais V, Skumryev V, Surinach S, Munoz JS, Baro MD: **Exchange bias in nanostructures.** *Phys Rep* 2005, **422**:65-117.
- Sort J, Nogues J, Surinach S, Munoz JS, Baro MD, Chappel E, Dupont F, Chouteau G: **Coercivity and squareness enhancement in ball-milled hard magnetic-antiferromagnetic composites.** *Appl Phys Lett* 2001, **79**:1142-1144.
- Gangopadhyay S, Hadjipanayis GC, Sorensen CM, Klabunde KJ: **Magnetic properties of ultrafine Co particles.** *IEEE Trans Magn* 1992, **28**:3174-3176.
- Meikleohn WH, Bean CP: **New magnetic anisotropy.** *Phys Rev* 1956, **102**:1413-1414.
- Berkowitz AE, Takano K: **Exchange anisotropy-a review.** *J Magn Magn Mater* 1999, **200**:552-570.
- Tang Y-K, Sun Y, Heng Z-H: **Cooling field dependence of exchange bias in phase-separated $\text{La}_{0.88}\text{Sr}_{0.12}\text{CoO}_3$.** *J Appl Phys* 2006, **100**:023914.
- Binek C, He X, Polisetty S: **Temperature dependence of the training effect in a Co/CoO exchange-bias layer.** *Phys Rev B* 2005, **72**:054408.
- Yi JB, Ding J: **Exchange coupling in CoO-Co bilayer.** *J Magn Magn Mater* 2006, **303**:e160-e164.
- Salazar-Alvarez G, Sort J, Surinach S, Baro MD, Nogues J: **Synthesis and size-dependent exchange bias in inverted core-shell MnO/ Mn_3O_4 nanoparticles.** *J Am Chem Soc* 2007, **129**:9102-9108.
- Kavich DW, Dickerson JH, Mahajan SV, Hasan SA, Park JH: **Exchange bias of singly inverted $\text{FeO}/\text{Fe}_3\text{O}_4$ core-shell nanocrystals.** *Phys Rev B* 2008, **78**:174414.
- Hajra P, Basu S, Dutta S, Brahma P, Chakravorty D: **Exchange bias in ferrimagnetic-antiferromagnetic nanocomposite produced by mechanical attrition.** *J Magn Magn Mater* 2009, **321**:2269-2275.
- Fiorani D, Del Bianco L, Testa AM: **Glassy dynamics in an exchange bias nanogranular system: Fe/FeO_x .** *J Magn Magn Mater* 2006, **300**:179-184.
- Amara D, Felner I, Nowik I, Margel S: **Synthesis and characterization of Fe and Fe_3O_4 nanoparticles by thermal decomposition of triiron dodecacarbonyl.** *Colloid Surf A-Physicochem Eng Asp* 2009, **339**:106-110.
- Ali-zade RA: **Magnetite nanoparticles with an antiferromagnetic surface layer.** *Inorg Mater* 2006, **42**:1215-1221.
- Gangopadhyay S, Hadjipanayis GC, Dale B, Sorensen CM, Klabunde KJ, Papaefthymiou V, Kosticas A: **Magnetic properties of ultrafine iron particles.** *Phys Rev B* 1992, **45**:9778-9787.

16. Zheng RK, Wen GH, Fung KK, Zhang XX: **Giant exchange bias and the vertical shifts of hysteresis loops in γ -Fe₂O₃-coated Fe nanoparticles.** *J Appl Phys* 2004, **95**:5244-5246.
17. Ishikawa Y, Shimizu Y, Sasaki T, Koshizaki N: **Boron carbide spherical particles encapsulated in graphite prepared by pulsed laser irradiation of boron in liquid medium.** *Appl Phys Lett* 2007, **91**:161110.
18. Wang HQ, Pyatenko A, Kawaguchi K, Li XY, Swiatkowska-Warkocka Z, Koshizaki N: **Selective pulsed heating for the synthesis of semiconductor and metal submicrometer spheres.** *Angew Chem-Int* 2010, **49**:6361-6364.
19. Pyatenko A, Yamaguchi M, Suzuki M: **Mechanisms of size reduction of colloidal silver and gold nanoparticles irradiated by Nd:YAG Laser.** *J Phys Chem C* 2009, **113**:9078-9085.
20. Fujii T, de Groot FMF, Sawatzky GA, Voogt FC, Hibma T, Okada K: **In situ XPS analysis of various iron oxide films grown by NO₂-assisted molecular-beam epitaxy.** *Phys Rev B* 1999, **59**:3195-3202.
21. Kodama RH, Berkowitz AE, McNiff EJ, Foner S: **Surface spin disorder in NiFe₂O₄ nanoparticles.** *Phys Rev Lett* 1996, **77**:394-397.
22. Kodama RH, Berkowitz AE, McNiff EJ, Foner S: **Surface spin disorder in ferrite nanoparticles.** *J Appl Phys* 1997, **81**:5552-5557.
23. Nogues J, Leighton C, Schuller IK: **Correlation between antiferromagnetic interface coupling and positive exchange bias.** *Phys Rev B* 2000, **61**:1315-1317.
24. Cornell RM, Schwertmann U: *The Iron Oxides: Structure, Properties, Reactions, Occurrences and Uses* Wiley-VCH, Weinheim; 2003.

doi:10.1186/1556-276X-6-226

Cite this article as: Swiatkowska-Warkocka et al.: Controlling exchange bias in Fe₃O₄/FeO composite particles prepared by pulsed laser irradiation. *Nanoscale Research Letters* 2011 **6**:226.

Submit your manuscript to a SpringerOpen[®] journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Immediate publication on acceptance
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► springeropen.com
