

NANO EXPRESS

Open Access

Synthesis and characterization of CuO nanowires by a simple wet chemical method

Anita Sagadevan Ethiraj and Dae Joon Kang*

Abstract

We report a successful synthesis of copper oxide nanowires with an average diameter of 90 nm and lengths of several micrometers by using a simple and inexpensive wet chemical method. The CuO nanowires prepared via this method are advantageous for industrial applications which require mass production and low thermal budget technique. It is found that the concentration and the quantity of precursors are the critical factors for obtaining the desired one-dimensional morphology. Field emission scanning electron microscopy images indicate the influence of thioglycerol on the dispersity of the prepared CuO nanowires possibly due to the stabilization effect of the surface caused by the organic molecule thioglycerol. The Fourier transform infrared spectrum analysis, energy dispersive X-ray analysis, X-ray diffraction analysis, and X-ray photoemission spectrum analysis confirm clearly the formation of a pure phase high-quality CuO with monoclinic crystal structure.

Introduction

Since the discovery of carbon nanotubes, the synthesis of one-dimensional morphology such as nanowires and nanorods has gained much attention because this constitutes an important building block of nanodevices and integrated nanosystems [1-5]. Among the available transition metal oxides, such as Ni, Cu, Zn, and Fe, synthesis of CuO is an important topic of research. Cupric oxide, CuO, which is a p-type semiconductor [6,7] (indirect bandgap of 1.2 to 1.5 eV) has been widely exploited for diverse applications, such as an active electrode material for Li-ion batteries, field emission [FE] emitters, heterogeneous catalysts, gas sensors, and solar cells [8-13]. Moreover, the evidence of a spin-dependent quantum transport phenomenon in CuO nanowires was already reported [14]. Till now, many methods have been developed to synthesize CuO nanowires or nanorods, such as thermal oxidation of copper foil, hydrothermal route, aqueous reaction, vapor-liquid-solid synthesis, solution-liquid-solid synthesis, laser ablation, arc discharge, precursor thermal decomposition, electron beam lithography, and template-assisted synthesis [5,15-19]. However, all these methods either require high temperatures, sophisticated instrumentation, inert

atmosphere, or long reaction time. The difference between the method in this manuscript and the aqueous reaction referred earlier is the starting precursor material used and the stabilizer. In our case, the precursor used is copper acetate, while in the aqueous reaction, copper chloride. We used the organic molecule thioglycerol [TG] as stabilizer, while no stabilizer was used in the latter case.

Moreover, until now, few reports are available in literature for the synthesis of CuO nanowires using the organic molecule TG. Therefore, in the present study, a systematic effort has been made to synthesize CuO nanowires by a simple and inexpensive wet chemical method using copper acetate and NaOH as the precursor material in the presence of organic molecule TG. The possible formation mechanism of CuO nanowires via this chemical method is also discussed.

Experimental detail

All the reagents were of analytical grade and were used without further purification. Copper acetate [(CH₃COO)₂-H₂O] and sodium hydroxide [NaOH] were used as precursors in the present experiment. Two separate solutions, copper acetate (0.5 M) in deionized [DI] water and NaOH (5 M) in DI water, were prepared. Aqueous copper acetate and aqueous NaOH solutions were referred to as solution A and solution B, respectively. Stirring is continued until the respective metal


* Correspondence: dj kang@skku.edu
BK21 Physics Research Division, Department of Energy Science, Institute of Basic Science, Sungkyunkwan University, 300 Cheoncheon-dong, Jangan-gu, Suwon, 440-746, South Korea

salts are completely dissolved in DI water. Later 1 μL of TG is added to solution A, and the solution is stirred for a few minutes. Solution B is then added to the reaction mixture, and water is immediately added. Further stirring continued for a few minutes. Centrifugation is done to collect the precipitate. Washing of the precipitate is carried out using the DI water for five to six times. Finally, the collected precipitate is dried overnight at 35°C.

The morphology of the CuO nanowires obtained in the present work was investigated by a field emission scanning electron microscope [FE-SEM] (JEOL JSM-7401F; JEOL Ltd., Akishima, Tokyo, Japan) operated at an accelerated voltage of 10 kV. The energy dispersive X-ray analysis [EDX] was carried out on the scanning electron microscopy [SEM] system. X-ray diffraction [XRD] spectra of the CuO samples were obtained using a powder X-ray diffractometer (D8 FOCUS 2200 V Bruker AXS, Bruker Optik GmbH, Ettlingen, Germany), using Cu $K\alpha$ radiation ($\lambda = 1.5418 \text{ \AA}$) with 2θ ranging from 20° to 80°. The Fourier transform infrared spectrum [FTIR] of CuO samples in the form of pellets was recorded using a Perkin Elmer 1615 spectrometer (PerkinElmer, Waltham, MA, USA). Pellets were prepared by mixing CuO powder with KBr, and spectrum was recorded in the range of 400 to 4,000 cm^{-1} . X-ray photoelectron spectroscopy [XPS] measurements were performed on ESCA MK II (VG Scientific Ltd., London, England) set up by using an Al $K\alpha$ X-ray source ($h\nu = 1486.6 \text{ eV}$). All the experiments were carried out at a base pressure of approximately 10^{-9} mbar, and a C 1s spectrum at $285.0 \pm 0.2 \text{ eV}$ served as the internal reference.

Results and discussion

CuO nanowires were synthesized by a wet chemistry route in the presence of organic molecule TG. Figure 1a represents the FE-SEM image of the as-synthesized CuO nanowires without TG, and Figure 1b, in the presence

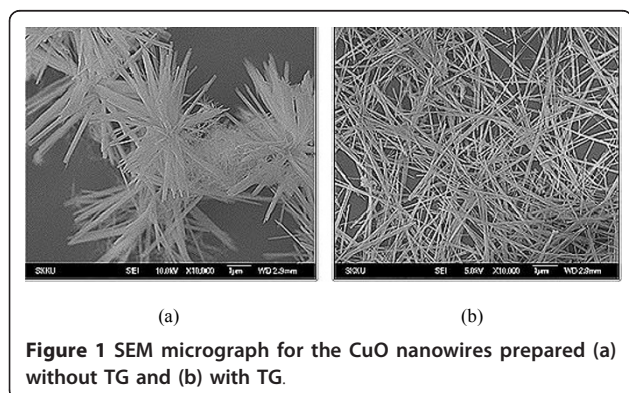

of TG. The morphology of the CuO samples without TG shows the formation of CuO flowers consisting of individual nanowires, whereas when the same synthesis is carried out in the presence of organic molecules TG, isolated CuO nanowires were obtained. Thus, the presence of a small amount of TG can render the nanowires of CuO well-dispersed, as seen clearly in the micrograph of CuO with TG. The average diameter of the CuO nanowires was observed to be around 90 nm with a length of about 2 to 5 μm .

In the synthesis of CuO nanowires, when copper acetate reacted with sodium hydroxide in the aqueous medium, the following reaction takes place as stated in Equation 1. This particular reaction does not involve any templates or substrates or any structure-directing agent like cetyltrimethylammonium-bromide [CTAB] or hexamethylene tetramine [HMTA] [20,21]. However, we introduced the organic molecule TG to the copper acetate solution before reacting with NaOH. In the present synthesis, the concentration of $\text{Cu}(\text{OAc})_2$ and NaOH and the reaction time are the critical parameters to obtain the nanowire morphology. Since the surface passivation of quantum dots using TG is well documented in literature [22,23], we have tried to utilize for the very first time the same organic molecule TG in the synthesis of CuO. From the SEM results, we observe that when no TG was used, we obtained CuO flowers consisting of individual nanowires. This result is in good agreement with the work reported by Zhu et al [24,25].



When the reaction in Equation 1 proceeds with the nucleation and crystal growth, the Gibbs free energy of the nanocrystallite surfaces is very high, and in order to decrease the Gibbs free energy, the nanocrystallites tend to aggregate [26]. Therefore, the flower morphology of CuO is obtained. However, when a small amount of TG is introduced in the synthesis of CuO, instead of a flower morphology, well-dispersed CuO nanowires are obtained, which can be speculated due to the stabilization effect caused by the use of organic molecule TG. Moreover, the role of TG is different from what structure-directing agents such as CTAB and HMTA are doing. In our case, without any structure-directing agent, we are able to generate CuO nanoflowers. When we carried out the CuO synthesis using TG, we obtained only separated CuO nanowires which clearly imply that the role of TG is definitely different from the role of CTAB and HMTA, where use of these agents leads to some kind of morphological changes in the material formation. Hence, the role of TG in our case is just for dispersion due to surface stabilization. An in-depth study is required, and further experiments are

underway to understand and investigate the exact mechanism and the role of TG in the synthesis of CuO nanowires.

In order to detect the elements present in the CuO samples, EDX analysis was carried out. The spectrum (not shown) indicates the presence of copper [Cu], oxygen [O], and silicon [Si]. No other impurity was detected. The presence of Si was from the substrate. Thus, the formation of CuO was confirmed from the EDX.

The X-ray diffraction pattern of the CuO samples prepared in the presence of TG is depicted in Figure 2. It can be clearly seen that all the peaks in the XRD patterns are consistent with the JCPDS data (48-1548) of the CuO with a monoclinic phase. No characteristic peaks of any other impurities such as Cu(OH)₂, Cu₂O, or precursors used are observed, indicating the formation of a pure phase CuO.

In order to understand the chemical and structural nature of the synthesized CuO and the effect of the chemicals used in the synthesis of CuO nanowires, FTIR analysis was carried out. Figure 3 represents the FTIR spectrum recorded for the CuO nanowires in the range of 400 to 4,000 cm⁻¹. The three characteristic bands observed at 432.3 cm⁻¹, 497 cm⁻¹, and 603.3 cm⁻¹ can be assigned to the Au mode, Bu mode, and the other Bu mode of CuO [27]. The high-frequency mode at 603.3 cm⁻¹ may be attributed to the Cu-O stretching along the [101] direction, while the peak at 497 cm⁻¹ can be assigned to the Cu-O stretching vibration along the [101] direction [28]. Moreover, no other IR active mode was observed in the range of 605 to 660 cm⁻¹, which totally rules out the existence of another phase, i.e., Cu₂O [29]. Moreover, the C-S bond observed at

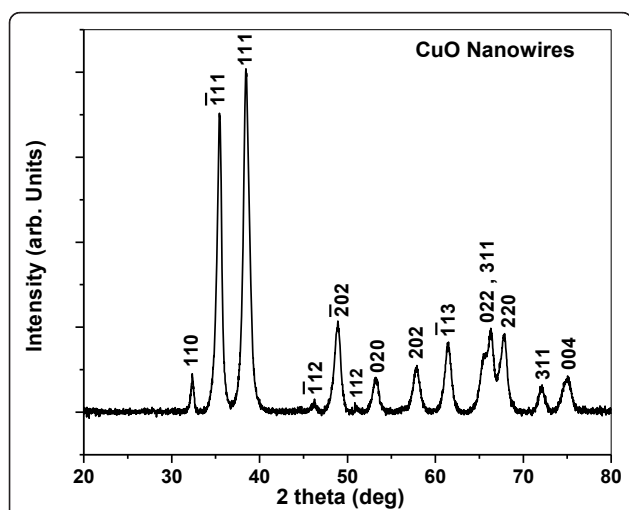


Figure 2 XRD pattern of the as-synthesized CuO nanowires with TG.

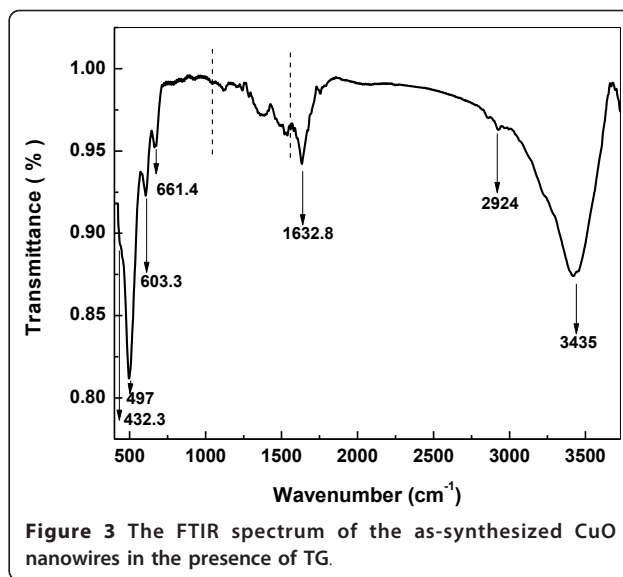


Figure 3 The FTIR spectrum of the as-synthesized CuO nanowires in the presence of TG.

661.4 cm⁻¹ can be attributed to the organic molecule TG used in the synthesis of CuO nanowires. Thus, the pure phase CuO with monoclinic structure is also confirmed from the FTIR analysis. The elemental composition and oxidation states of the CuO samples were analyzed using XPS. The survey scan recorded (not shown) for the sample shows the presence of Cu and O. A trace amount of sulfur which is detected comes from the TG. A selected area scan is also recorded for the individual elements (Cu 2p, S 2p, and O 1s) and is shown in Figure 4a, b, c, respectively. The Cu 2p core-level spectrum (Figure 4a) represents two peaks located at 934 and 953.8 eV which corresponds to the Cu 2p_{3/2} and Cu 2p_{1/2}, respectively. These values match well

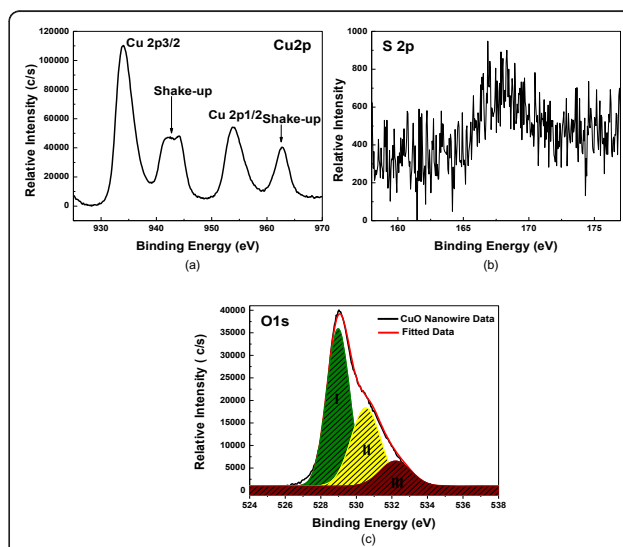


Figure 4 X-ray photoelectron spectra. (a) Cu 2p, (b) S 2p, and (c) O 1s deconvolution of the CuO nanowires synthesized with TG.

with the data reported for the Cu(2p) in CuO [18,30-32]. Also, the width of approximately 19.8 eV between these two Cu peaks is the same as in the standard spectrum of Cu. In addition, the shake-up satellite peaks located at 942.7 eV and 944.8 eV are at a higher binding energy value of 8.8 and 10.1 eV, respectively, when compared with the main sharp peak of Cu 2p_{3/2} located at 934 eV [30]. The strong shake-up satellites recorded in the CuO sample confirm the Cu (II) oxidation state and rule out the possibility of the existence of a Cu₂O phase [18,32]. The O 1s core level spectrum is shown in Figure 4c, which demonstrates a broad Gaussian peak and is deconvoluted as peaks I, II, and III, respectively. The peak I at the low binding energy value of 529 eV is due to the oxygen in the CuO crystal lattice, which corresponds to the O-Cu bond, whereas the peaks II and III located at the higher binding energy values of 530.5 eV and 532.3 eV are due to the chemisorbed oxygen caused by surface hydroxyl groups which are associated with the O-H bond [18]. From the elemental scan of sulfur (Figure 4b), one can see that a small amount of sulfur detected in XPS indicates the presence of TG on the surface of the CuO nanowires synthesized.

Conclusions

Using a simple and inexpensive wet chemical method, the synthesis of copper oxide nanowires with diameters of 90 nm and lengths of several micrometers has been successfully carried out. The concentration and quantity of precursors are the critical factors for obtaining the desired 1-D morphology. SEM micrographs clearly indicate the influence of TG on the dispersity of the prepared CuO nanowires which may be due to the stabilization effect of the surface caused by the organic molecule TG. The FTIR and XPS data analyses confirm the formation of a pure phase CuO with monoclinic crystal structure. EDX and XRD data support the same finding.

Acknowledgements

This work was supported by the Korea Science and Engineering Foundation (KOSEF) and the National Research Foundation of Korea (NRF) grants funded by the Korean government (KRF-2006-311-C00050), R31-2008-000-10029-0 (World Class University Program), and 2011-0011775 (Basic Science Research Project).

Authors' contributions

ASE did the synthesis and performed tests on the samples. DJK conceived and designed the experiments. ASE and DJK wrote the manuscript. All authors read and approved the final manuscript.

Competing interests

The authors declare that they have no competing interests.

Received: 13 September 2011 Accepted: 5 January 2012

Published: 5 January 2012

References

1. Patzke GR, Krumeich F, Nesper R: Oxidic nanotubes and nanorods-anisotropic modules for a future nanotechnology. *Angew Chem Int Ed* 2002, **41**:2446-2461.
2. Dekker C: Carbon nanotubes as molecular quantum wires. *Phys Today* 1999, **52**:22.
3. Huang Y, Duan XF, Cui Y, Lauhon LJ, Kim KH, Lieber CM: Logic gates and computation from assembled nanowire building blocks. *Science* 2001, **294**:1313-1317.
4. Hu J, Odom TW, Lieber CM: Chemistry and physics in one dimension: synthesis and properties of nanowires and nanotubes. *Acc Chem Re* 1999, **32**:435-445.
5. Martel R, Schmidt T, Shea HR, Hertel T, Avouris P: Single- and multi-wall carbon nanotube field-effect transistors. *Appl Phys Lett* 1998, **73**:2447-2449.
6. Marabelli F, Parravicini GB, Salghetti-Drioli F: Optical gap of CuO. *Phys Rev B* 1995, **52**:1433-1436.
7. Fan H, Yang L, Hua W, Wu X, Wu Z, Xie S, Zou B: Controlled synthesis of monodispersed CuO nanocrystals. *Nanotechnology* 2004, **15**:37-42.
8. Switzer JA, Kothari HM, Poizot P, Nakanishi S, Bohannan EW: Enantiospecific electrodeposition of a chiral catalyst. *Nature* 2003, **425**:490-493.
9. Anandan S, Wen X, Yang S: Room temperature growth of CuO nanorod arrays on copper and their application as a cathode in dye-sensitized solar cells. *Mater Chem Phys* 2005, **93**:35-40.
10. Chowdhuri A, Sharma P, Gupta V, Sreenivas K, Rao KV: H₂S gas sensing mechanism of SnO₂ films with ultrathin CuO dotted islands. *J Appl Phys* 2002, **92**:2172-2180.
11. Bennici S, Gervasini A: Catalytic activity of dispersed CuO phases towards nitrogen oxides (N₂O, NO, and NO₂). *Appl Catal B* 2006, **62**:336-344.
12. Ghosh S, Avasthi DK, Shah P, Ganesan V, Gupta A, Sarangi D, Bhattacharya R, Assmann W: Deposition of thin films of different oxides of copper by RF reactive sputtering and their characterization. *Vacuum* 2000, **57**:377-385.
13. Hsieh CT, Chen JM, Lin HH, Shin HC: Field emission from various CuO nanostructures. *Appl Phys Lett* 2003, **83**:3383-3385.
14. Gillingham DM, Müller C, Hong J, Wu RQ, Bland JAC: Evidence of spin-dependent quantum transport effects in CuO nanowires. *J Phys Cond Matter* 2006, **18**:9135-9142.
15. Kaur M, Muthe KP, Deshpande SK, Choudhury S, Singh JB, Verma N: Growth and branching of CuO nanowires by thermal oxidation of copper. *J Cryst Growth* 2006, **289**:670-675.
16. Cao MH, Wang YH, Guo CX, Qi YJ, Hu CW, Wang EB, Nanosci J: A simple route towards CuO nanowires and nanorods. *Nanotech* 2004, **4**:824-828.
17. Wang WZ, Varghese OK, Ruan CM, Paulose M, Grimes CA: Synthesis of CuO and Cu [sub 2] O crystalline nanowires using Cu (OH)[sub 2] nanowire templates. *J Mater Res* 2003, **18**:2756-2759.
18. Xu C, Lin Y, Xu G, Wang G: Preparation and characterization of CuO nanorods by thermal decomposition of Cu₂O₄ precursor. *Mater Res Bull* 2002, **37**:2365-2372.
19. Jiang XC, Herricks T, Xia YN: CuO nanowires can be synthesized by heating copper substrates in air. *Nano Lett* 2002, **2**:1333-1338.
20. Zhang H, Yang D, Ji Y, Ma X, Xu J, Que D: Low temperature synthesis of flowerlike ZnO nanostructures by cetyltrimethylammonium bromide-assisted hydrothermal process. *J Phys Chem B* 2004, **108**:3955-3958.
21. Gao X, Li X, Yu W: Flowerlike ZnO nanostructures via hexamethylenetetramine-assisted hydrolysis of zinc-ethylenediamine complex. *Phys Chem B* 2005, **109**:1155-1161.
22. Ethiraj AS, Hebalkar N, Kulkarni SK, Pasricha R, Dem C, Schmitt M, Kiefer W, Weinhardt L, Joshi S, Fink R, Heske C, Kumpf C, Umbach E: Enhancement of photoluminescence in manganese-doped ZnS nanoparticles due to a silica shell. *J Chem Phys* 2003, **118**:8945-8953.
23. Khosravi AA, Kundu MM, Kuruvilla BA, Shekhawat GS, Gupta RP, Sharma AK, Vyas PD, Kulkarni SK: Manganese doped zinc sulphide nanoparticles by aqueous method. *Appl Phys Lett* 1995, **67**:2506-2508.
24. Zhu J, Chen H, Liu H, Yang X, Lu L, Wang X: Needle-shaped nanocrystalline CuO prepared by liquid hydrolysis of Cu(OAc)₂. *Mater Sci and Eng* 2004, **A 384**:172-176.
25. Zhu J, Bi H, Wang Y, Wang X, Yang X, Lu L: Synthesis of flower-like CuO nanostructures via a simple hydrolysis route. *Mater Lett* 2007, **61**:5236-5238.

26. Wang JZ, Xu J, Zhu J, Chen HY: **Preparation of CuO nanoparticles by microwave irradiation.** *J Cryst Growth* 2002, **244**:88-94.
27. Nyquist RA, Kagel RO: *Infrared Spectra of Inorganic Compounds* New York and London: Academic Press; 1997, 220.
28. Kliche K, Popovic ZV: **Far-infrared spectroscopic investigations on CuO.** *Phys Rev B* 1990, **42**:10060-10066.
29. Zheng L, Liu X: **Solution-phase synthesis of CuO hierarchical nanosheets at near-neutral pH and near-room temperature.** *Mater Lett* 2007, **61**:2222-2226.
30. Moulder J, Sticke W, Sobol P, Bomben K: **Standard ESCA spectra of the elements and line energy information.** In *Handbook of X-ray Photoelectron Spectroscopy*. Edited by: Chastain J. USA: Perkin Elmer Cooperation: Physical Electronics Division; 1992.
31. Hong ZS, Cao Y, Deng JF: **A convenient alcohothermal approach for low temperature synthesis of CuO nanoparticles.** *Mater Lett* 2002, **52**:34-38.
32. Zarate RA, Hevia F, Fuentes S, Fuenzalida VM, Zuniga A: **Novel route to synthesize CuO nanoplatelets.** *J Solid State Chem* 2007, **180**:1464-1469.

doi:10.1186/1556-276X-7-70

Cite this article as: Ethiraj and Kang: **Synthesis and characterization of CuO nanowires by a simple wet chemical method.** *Nanoscale Research Letters* 2012 **7**:70.

Submit your manuscript to a SpringerOpen® journal and benefit from:

- ▶ Convenient online submission
- ▶ Rigorous peer review
- ▶ Immediate publication on acceptance
- ▶ Open access: articles freely available online
- ▶ High visibility within the field
- ▶ Retaining the copyright to your article

Submit your next manuscript at ▶ springeropen.com
