

NANO EXPRESS

Open Access

Unique and facile solvothermal synthesis of mesoporous WO₃ using a solid precursor and a surfactant template as a photoanode for visible-light-driven water oxidation

Dong Li¹, Debraj Chandra¹, Kenji Saito¹, Tatsuto Yui¹ and Masayuki Yagi^{1,2*}

Abstract

Mesoporous tungsten trioxide (WO₃) was prepared from tungstic acid (H₂WO₄) as a tungsten precursor with dodecylamine (DDA) as a template to guide porosity of the nanostructure by a solvothermal technique. The WO₃ sample (denoted as WO₃-DDA) prepared with DDA was moulded on an electrode to yield efficient performance for visible-light-driven photoelectrochemical (PEC) water oxidation. Powder X-ray diffraction (XRD) data of the WO₃-DDA sample calcined at 400°C indicate a crystalline framework of the mesoporous structure with disordered arrangement of pores. N₂ physisorption studies show a Brunauer-Emmett-Teller (BET) surface area up to 57 m² g⁻¹ together with type IV isotherms and uniform distribution of a nanoscale pore size in the mesopore region. Scanning electron microscopy (SEM) images exhibit well-connected tiny spherical WO₃ particles with a diameter of ca. 5 to 20 nm composing the mesoporous network. The WO₃-DDA electrode generated photoanodic current density of 1.1 mA cm⁻² at 1.0 V versus Ag/AgCl under visible light irradiation, which is about three times higher than that of the untemplated WO₃. O₂ (1.49 μmol; Faraday efficiency, 65.2%) was evolved during the 1-h photoelectrolysis for the WO₃-DDA electrode under the conditions employed. The mesoporous electrode turned out to work more efficiently for visible-light-driven water oxidation relative to the untemplated WO₃ electrode.

Keywords: Tungsten trioxide; Mesoporous structure; Photoelectrocatalysis; Water oxidation

Background

The recent advances in nanostructured materials have expanded their potential applications in much-desired materials for efficient solar energy conversion [1-6]. Photoelectrochemical (PEC) water splitting into oxygen and hydrogen is an attractive but challenging way for the conversion of solar energy, [7] following the pioneer work on a TiO₂ photoanode for water splitting by Honda and Fujishima [8]. Unfortunately, owing to its wide electronic bandgap (3.0 to 3.2 eV), TiO₂ absorbs only an ultraviolet fraction of a solar spectrum (which accounts for just 4% of solar irradiation), being conse-

quently responsible for low efficiency in utilization of solar light [2,7,9]. For solar water splitting, intensive researches have been focused on nanostructured materials with narrow bandgaps including WO₃ [3,4,10-19]. WO₃, an n-type semiconductor, has attracted immense attention as a photoanode material for water oxidation in PEC cells because of its visible light response (bandgap, $E_g = 2.6$ to 2.8 eV), a valence band edge position thermodynamically possible for water oxidation (about 3 V versus the normal hydrogen electrode), and good photochemical stability under the acidic conditions [3,10-12,20-24].

Porous material design, which has been developed employing template-directed approaches using small organic compounds [25], supramolecular assembly [26], and polymer beads [27], is of great importance in many research fields because of the high porosity, large area per unit volume, and favorable design of a porous structure [25,28,29]. So far, several efforts in nanostructural and

* Correspondence: yagi@eng.niigata-u.ac.jp

¹Department of Materials Science and Technology, Faculty of Engineering, Niigata University, 8050 Ikarashi-2, Niigata 950-2181, Japan

²Precursory Research for Embryonic Science and Technology (PRESTO), Japan Science and Technology Agency (JST), 4-1-8 Honcho, Kawaguchi, Saitama 332-0012, Japan

porosity controls of WO_3 have been provided to increase the contact area between an electrode and an electrolyte solution and to make electron transport in WO_3 films more efficient, enhancing performance of PEC water oxidation at WO_3 electrodes [3,11,30-33]. For example, Santato et al. have reported that crystalline WO_3 photoanodes with interconnected nanoparticulate structures improved photoelectrochemical properties [30-32]. Berger et al. have demonstrated that random porous layers of WO_3 produced significantly higher photocurrent efficiency than a compact layer [33]. Our group recently demonstrated a crystalline small mesoporous network of a WO_3 photoanode for high improvement in performance of PEC water oxidation [3].

Numerous methods have been employed to control the dimension, morphology, and crystal structure of WO_3 , e.g., vacuum evaporation [34], chemical vapor deposition [35,36], sol-gel precipitation [22,30-32], hydrothermal/solvothermal [37-40], surfactant/hard template techniques [3,41,42], and so on. Among the abundant methods, hydrothermal/solvothermal techniques can provide a cost-effective and one-step route synthesis of WO_3 [37-40]. Although the surfactant template techniques require a liquid tungsten precursor to utilize interaction with a surfactant in principle, we have focused on the interaction between a solid tungsten precursor and a surfactant under solvothermal conditions to yield mesoporous WO_3 . Herein, we report the unique and facile synthesis of mesoporous WO_3 utilizing solid H_2WO_4 as a tungsten precursor with an organic amphiphilic molecule, dodecylamine (DDA), as a surfactant template for porosity of the nanostructure. The mesoporous WO_3 exhibited high surface area and improved the performance of PEC water oxidation compared to the corresponding materials prepared without a template.

Methods

Materials

Tungstic acid (H_2WO_4) was purchased from Kanto Chemical Co., Inc. (Chuo-ku, Tokyo, Japan). DDA was obtained from Sigma-Aldrich (St. Louis, MO, USA). Polyethylene glycol (PEG, molecular weight = 2,000) was obtained from Wako Chemical Co. (Osaka, Japan). Marpolose (60MP-50) was purchased from Matsumoto Yushi-Seiyaku Co. (Osaka, Japan). An indium tin oxide (ITO)-coated glass substrate was obtained from Asahi Glass Co. (Tokyo, Japan). Millipore water (Merck Ltd., Tokyo, Japan) was used for all the experiments. All other chemicals unless mentioned otherwise were of analytical grade and used as received.

Synthesis of mesoporous WO_3

In a typical synthesis, 1.7 g of DDA (9.0 mmol) was dissolved in 15 mL ethanol under stirring at room

temperature. Tungstic acid (0.9 g; 3.6 mmol) was added to the DDA solution with stirring for 30 min to yield a suspension. It was transferred to a Teflon-lined stainless steel autoclave and then placed in an oil bath at 150°C for 24 h. After the autoclave was cooled down to room temperature, the solid product was recovered by centrifugation, then washed repeatedly by ethanol and air-dried. The solid product was calcined at 400°C with a rate of 1°C min^{-1} and then maintained at 400°C for 1 h in flowing N_2 , followed by changing to O_2 flow (at 400°C) for 2 h to result in a WO_3 sample (denoted as WO_3 -DDA). A control sample (denoted as WO_3 -bulk) was prepared in the same manner except for the addition of DDA.

Preparation of electrodes

The WO_3 film-coated ITO electrodes (ITO/ WO_3) were prepared employing a doctor-blade technique. Before coating, ITO glass substrates (1.0 cm^2 area) were cleaned up by a UV-ozone treatment (photo surface processor PL16-110, Sen Lights Co., Osaka, Japan) for 15 min. In a typical procedure, WO_3 powder (200 mg), PEG (100 mg), and Marpolose (20 mg) were mixed in 300 μL of water. The mixture suspension was stirred for approximately 2 to 4 h until a smooth paste was formed. The resulting paste was squeezed over an ITO glass substrate by a doctor-blade coater and dried at 80°C for 15 min. After repeating the procedure for two times, the electrodes were calcined at 400°C and maintained at 400°C in flowing N_2 for 1 h, followed by changing to O_2 flow (at 400°C) for 2 h.

Structural characterization

Characterization of the morphological features and the crystalline phase was conducted by field-emission scanning electron microscopy (FESEM; JSM-6500 F, JEOL Ltd., Akishima, Tokyo, Japan) and powder X-ray diffraction (XRD; MiniFlexII, Rigaku Corporation, Tokyo, Japan) using monochromated $\text{Cu K}\alpha$ ($\lambda = 1.54 \text{ \AA}$) radiation. Nitrogen adsorption-desorption isotherms were measured using a BELSORP-miniIII (BEL Japan, Inc., Osaka, Japan) at 77 K. Prior to gas adsorption, samples were degassed in vacuum for 4 h at 150°C . The Brunauer-Emmett-Teller (BET) method was utilized to calculate the surface areas. The pore size distributions were obtained from analysis of the adsorption branches of the isotherms by the Barrett-Joyner-Halenda (BJH) method. Fourier transform infrared spectra were recorded on a Jasco FT/IR-4200 spectrophotometer (Jasco Inc., Tokyo, Japan).

Photoelectrochemical measurements

Photoelectrochemical measurement was carried out in a two-compartment photoelectrochemical cell separated by a Nafion membrane using an electrochemical analyzer (HZ-3000, Hokuto Denko Co. Ltd., Tokyo, Japan). A three-electrode system has been employed by using ITO/ WO_3

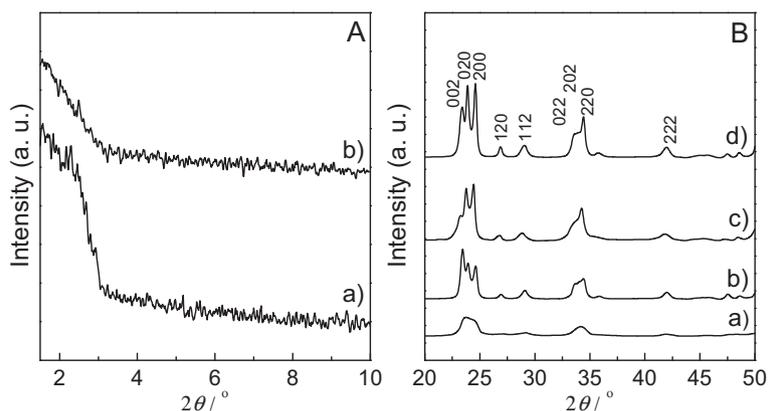


Figure 1 Small-angle and wide-angle X-ray diffraction patterns. (A) Small-angle and (B) wide-angle XRD patterns of WO_3 -DDA and WO_3 -bulk samples after being calcined at 400°C and 500°C. (a) WO_3 -DDA calcined at 400°C, (b) WO_3 -DDA calcined at 500°C, (c) WO_3 -bulk calcined at 400°C, and (d) WO_3 -bulk calcined at 500°C.

and Ag/AgCl electrodes in one compartment as the working and reference electrodes, respectively, and a Pt wire in the other compartment as the counter electrode. An aqueous 0.1 M phosphate solution was used as an electrolyte in both compartments of the cell, which was saturated with Ar gas prior to the measurement. The cyclic voltammogram (CV) was recorded at a scan rate of 50 mV s^{-1} at 25°C. Light ($\lambda > 390 \text{ nm}$) was irradiated from the backside of the working electrode using a 500-W xenon lamp (Optical ModuleX; Ushio Inc., Tokyo, Japan) with a UV-cut filter (L39) and liquid filter (0.2 M CuSO_4) for cutting of heat ray. The output of light intensity was calibrated as 100 mW cm^{-2} using a spectroradiometer (USR-40; Ushio Inc., Tokyo, Japan). Photoelectrocatalysis was conducted under the potentiostatic conditions of 0.5 V versus Ag/AgCl at 25°C under illumination of light ($\lambda > 390 \text{ nm}$, 100 mW cm^{-2}) for

1 h. The amounts of H_2 and O_2 evolved were determined from the analysis of the gas phase (headspace volume: 87.3 mL) of counter and working electrode compartments, respectively, using gas chromatography (GC-8A with a TCD detector and molecular sieve 5A column and Ar carrier gas; Shimadzu Corporation, Kyoto, Japan).

Results and discussion

The powder XRD patterns of the WO_3 samples calcined at 400°C and 500°C are shown in Figure 1. Small-angle XRD patterns (Figure 1 (a)) of WO_3 -DDA at 400°C showed a single diffraction peak at low 2θ , being a sign of formation of mesoporous structures, but the weak intensity and broadness of the peak are possibly due to disordered mesoporous structures. The d -spacing, calculated from the XRD peak at $2\theta = 2.3^\circ$ is 3.78 nm. Weakening of the intensity of the diffraction peak for

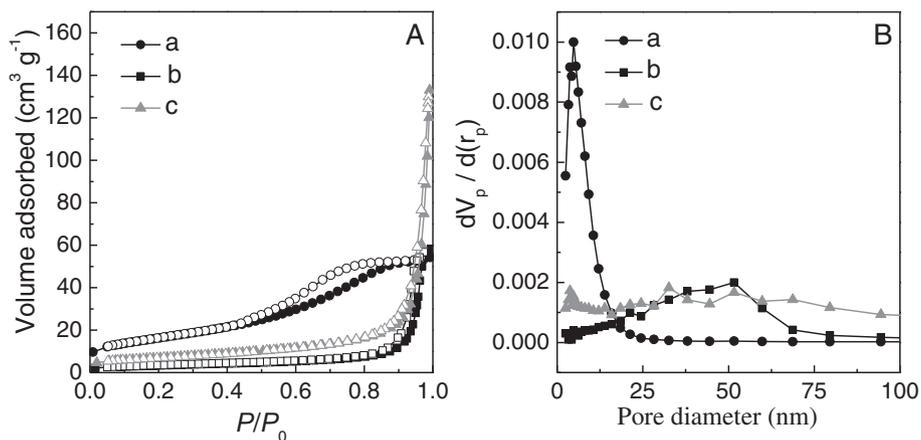


Figure 2 N_2 sorption isotherms and pore size distribution. (A) N_2 sorption isotherms and (B) pore size distribution of WO_3 -DDA and WO_3 -bulk samples after being calcined at 400°C and 500°C. In N_2 sorption, isotherm adsorption and desorption points are marked by filled and empty symbols, respectively. (a) WO_3 -DDA calcined at 400°C, (b) WO_3 -DDA calcined at 500°C, and (c) WO_3 -bulk calcined at 400°C.

Table 1 Physicochemical properties of WO₃ samples

Sample name	Calcination temperature (°C)	<i>d</i> -spacing (nm)	Surface area (m ² g ⁻¹)	Pore volume (cm ³ g ⁻¹)	Pore size (nm)>
WO ₃ -DDA	400	1.70	57	0.08	4.9
WO ₃ -DDA	500	-	12	0.09	48.2
WO ₃ -bulk	400	-	24	0.19	52.7

WO₃-DDA at 500°C (Figure 1 (b)) suggests degradation of the mesostructure at higher temperature. The wide-angle XRD patterns of both the WO₃-DDA and WO₃-bulk samples revealed crystallization of the framework after calcination at 400°C and higher degree of crystallization at 500°C, though crystallinity of WO₃-bulk seems to be higher than that of WO₃-DDA at both calcination temperatures. The *d*-spacings calculated from the XRD peaks of both WO₃-DDA and WO₃-bulk were in good agreement with phase-pure monoclinic WO₃ (JCPDS number: 43-1305). Average crystallite sizes for WO₃-DDA, estimated using [002] reflections were 5.7 and 11.6 nm at 400°C and 500°C, respectively, which suggests that progressive growth of the WO₃ nanocrystal in the porous network is responsible for degradation of the mesostructure at 500°C.

N₂ adsorption/desorption isotherms of the WO₃ samples calcined at 400°C and 500°C are shown in Figure 2. The isotherm (Figure 2 (a)) of WO₃-DDA calcined at 400°C could be classified as type IV, characteristic of mesoporous materials [26,43]. In this isotherm, the adsorption amount gradually increased in a range of $P/P_0 = 0.4$ to

0.85, which could be explained by the classical capillary condensation observed for mesopores. The H2 hysteresis loop in the isotherm (Figure 2 (a)) may be caused by roughness of the pore and particle surface [44]. The BET surface area and mesopore volume for WO₃-DDA calcined at 400°C were 57 m² g⁻¹ and 0.08 cm³ g⁻¹, respectively, as summarized in Table 1. The pore size distribution (Figure 2) by the BJH method shows narrow distribution with a peak pore width at 4.9 nm. Isotherm of WO₃-DDA calcined at 500°C shows a predominantly type II nature, and the BET surface area was drastically reduced to 12 m² g⁻¹. The pore size distribution of WO₃-DDA calcined at 500°C gives a wider peak at approximately 50 nm due to large interparticle pores. These results are in accordance with the degradation of the mesoporous structure of WO₃-DDA due to progressive growth of WO₃ nanocrystals at higher temperature of 500°C, as observed in the XRD measurement. The WO₃-bulk sample synthesized without DDA exhibited typical type II isotherms, characteristic of nonporous solids. The BET surface area is 24 m² g⁻¹ at 400°C, which is noticeably low compared to the mesoporous WO₃-DDA.

The Fourier transform infrared (FTIR) spectra of as-made (before calcination) and calcined (400°C and 500°C) WO₃-DDA samples are shown in Figure 3. C-H stretching vibration bands of the hydrocarbon chains at 2,919 cm⁻¹ (asymmetric) and 2,844 cm⁻¹ (symmetric) along with C-H bending vibration bands at 1,469 cm⁻¹ of CH₂ groups were clearly observed in the as-made sample. Comparing the FTIR spectra of the as-made WO₃-DDA with calcined WO₃-DDA samples, we could see that peaks due to C-H vibration diminished completely for the calcined samples. This indicates complete removal of DDA during calcination at 400°C and 500°C, which is very much necessary to generate high porosity for these mesoporous materials.

The scanning electron microscopy (SEM) images of the calcined WO₃-DDA samples are shown in Figure 4. The SEM images of the top view (Figure 4a,b) exhibit that a mesoporous network is composed of tiny spherical WO₃ particles of *ca.* 5 to 20 nm in diameter, being well connected to each other. In a few places, the spherical particles agglomerate to form large particles. A close look into these images suggests that the average dimension of particles increases with calcination temperature from 400°C to 500°C due to sintering of WO₃ nanocrystals at higher calcination temperature. After preparation of a

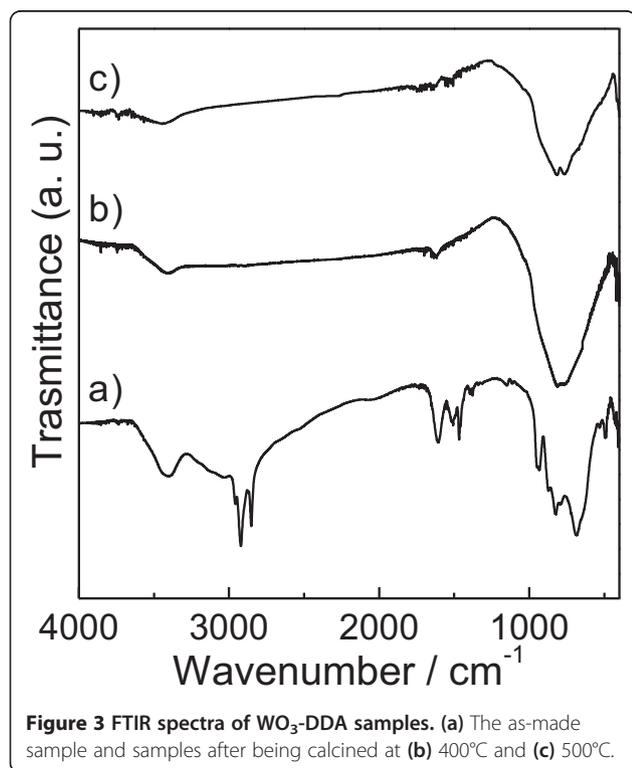


Figure 3 FTIR spectra of WO₃-DDA samples. (a) The as-made sample and samples after being calcined at (b) 400°C and (c) 500°C.

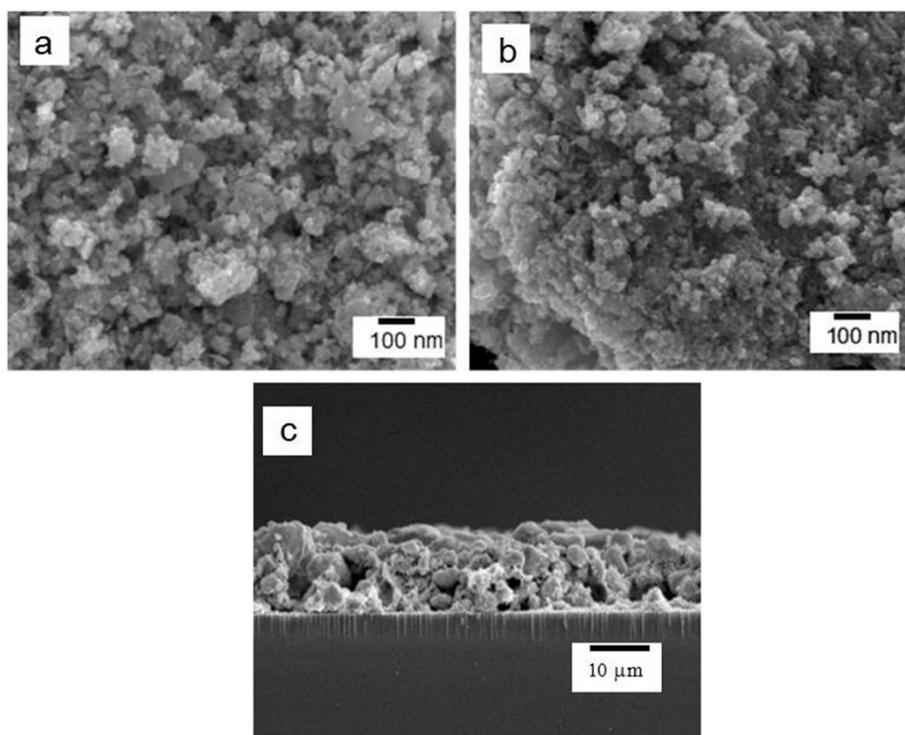


Figure 4 Scanning electron microscopic (SEM) images. Top view of WO_3 -DDA samples calcined at (a) 400°C and (b) 500°C. (c) Cross-sectional view of the ITO/ WO_3 -DDA electrode after being calcined at 500°C.

mesoporous WO_3 film on an ITO electrode, the film thickness was measured to be *ca.* 12 μm from the cross-sectional SEM image (Figure 4c). This crystalline mesoporous structure of the connected WO_3 particles is important to yield a large interface between the electrolyte and film as well as efficient electron transport through the film, which are consequently expected to work efficiently for

PEC water oxidation since the electron and hole pairs generated by photoexcitation of WO_3 would have less chance to recombine before participating in a water oxidation reaction at the WO_3 surface.

The PEC properties of the ITO/ WO_3 electrodes were studied in a 0.1 M phosphate solution. Figure 5 shows the CVs of the ITO/ WO_3 electrodes. On CVs of samples


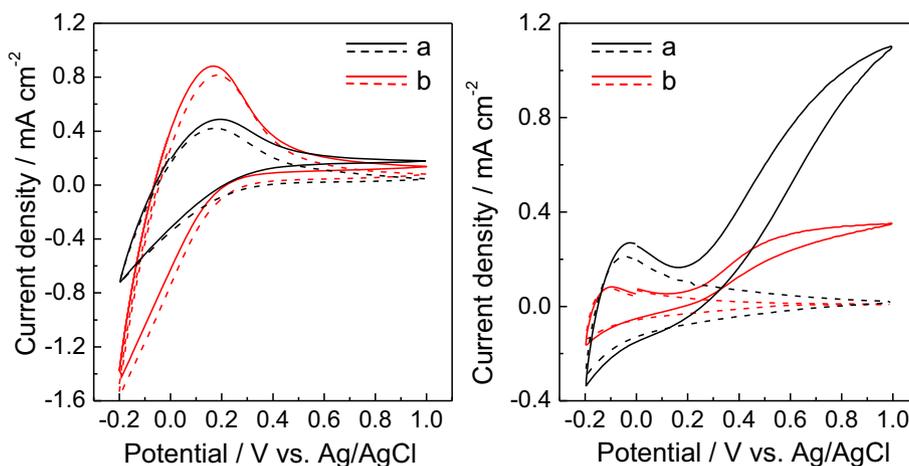


Figure 5 Cyclic voltammograms (CVs) for samples calcined at 400°C (left) and 500°C (right). (a) ITO/ WO_3 -DDA and (b) ITO/ WO_3 -bulk electrodes in a 0.1 M phosphate buffer solution with pH = 6.0. The dashed and solid lines represent CVs measured in the dark and upon irradiation of visible light ($\lambda > 390 \text{ nm}$, 100 mW cm^{-2}), respectively.

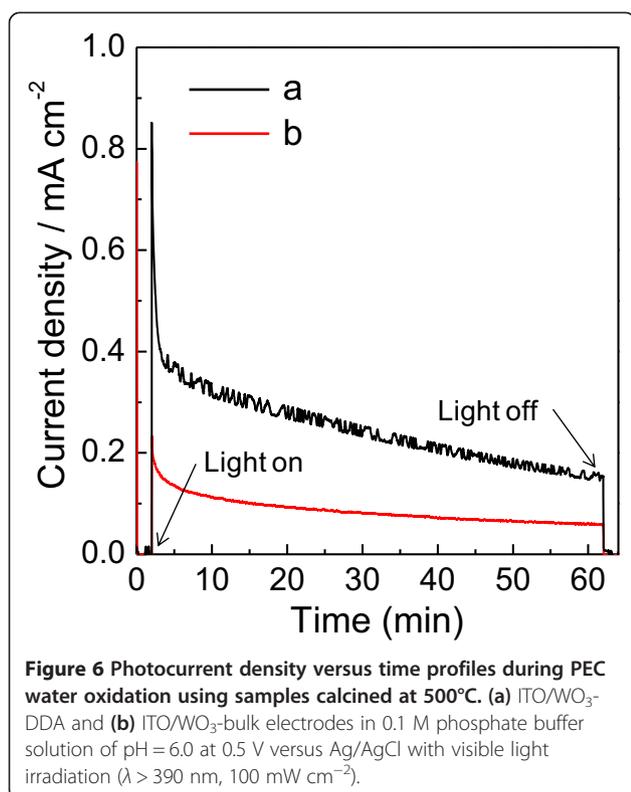

calcined at 400°C for both WO₃-DDA and WO₃-bulk (Figure 5, left), no redox response was observed in the dark in a potential range of 0.4 ~ 1.0 V versus Ag/AgCl except for a response based on WO₃/H_xWO₃ below 0.2 V. Upon irradiation of visible light, the anodic current (0.13 ~ 0.18 mA cm⁻² at 1.0 V versus Ag/AgCl) was hardly generated for both samples. This is ascribed to insufficient crystallinity of both WO₃-DDA and WO₃-bulk calcined at 400°C. Crystallinity rather than porosity for samples calcined at 400°C is a dominant factor for the PEC performance of the WO₃-based photoanode under the conditions employed [20,32]. On CVs of the samples calcined at 500°C (Figure 5, right), the significantly high photoanodic current due to water oxidation was observed upon visible light irradiation above an onset potential of 0.17 V versus Ag/AgCl due to higher crystallinity. The photoanodic current reached 1.1 mA cm⁻² at 1.0 V for WO₃-DDA, which is about three times higher compared to that for the WO₃-bulk (0.36 mA cm⁻² at 1.0 V) electrode in spite of the degradation of mesoporous structure for WO₃-DDA calcined at 500°C.

The degraded mesoporous structure for WO₃-DDA might result in favorable conditions for PEC water oxidation compared with the nanoparticle structure of WO₃-bulk. Otherwise, another important factor might be involved in the higher performance of the WO₃-DDA electrode. In the present paper, we do not pursue interpretation of the higher performance of the WO₃-DDA electrode because our attention is on the solvothermal synthesis of a mesoporous structure of WO₃.

Photoelectrocatalysis over the ITO/WO₃ electrodes was conducted in a 0.1 M phosphate solution (pH = 6.0) under potentiostatic conditions at 0.5 V versus Ag/AgCl for 1 h upon visible light irradiation ($\lambda > 390$ nm, 100 mW cm⁻²). The photocurrent-time profiles of both WO₃-DDA and WO₃-bulk calcined at 500°C exhibit initial spikes in the photocurrent upon illumination (related with the capacitance component at the solid-liquid interface), followed by a photocatalytic current, as shown in Figure 6. The photocurrent density of WO₃-DDA at 1 min was 0.37 mA cm⁻², which is 2.5 times higher than that of the WO₃-bulk (0.15 mA cm⁻² at 1 min) electrode. The charge amount passed during 1-h photoelectrocatalysis for WO₃-DDA (0.89 C) was 3.9 times higher than that of WO₃-bulk (0.23 C). As a consequence of the high charge amount, the markedly high amount ($n_{O_2} = 1.5$ μ mol, Faradaic efficiency (FE_{O₂) = 65%) of O₂ evolved for the WO₃-DDA electrode compared to that ($n_{O_2} = 0.4$ μ mol, FE_{O₂) = 58%) of the WO₃-bulk electrode, as summarized in Table 2. As compared with performances of PEC water oxidation under the same conditions for WO₃-based photoanodes reported earlier [3], the performance of the present mesoporous WO₃-DDA is lower than that of the small mesoporous WO₃ film ($n_{O_2} = 4.2$ μ mol, FE_{O₂) = 79%) [3], but much higher than that of interparticle mesoporous WO₃ ($n_{O_2} = 0.9$ μ mol, FE_{O₂) = 61%) and bulk WO₃ ($n_{O_2} = 0.4$ μ mol, FE_{O₂) = 44%) [3]. The high performance of the mesoporous WO₃-DDA photoanode is attributed to its high surface-to-volume ratio which offers a large number of water oxidation sites at the electrolyte-WO₃ interface, and well-connected WO₃ particles for efficient electron transport through the film.}}}}}

Conclusions

We have prepared mesoporous WO₃ materials by a unique and facile solvothermal method using solid H₂WO₄ as a tungsten precursor. DDA was used as a template for the

Table 2 Summary of photoelectrocatalytic water oxidation at different ITO/WO₃ photoanodes calcined at 500°C in 0.1 M phosphate solution

Sample name	Charge (C)	n_{O_2} (μ mol)	FE _{O₂} ^a (%)	$n_{H_2}^b$ (μ mol)	FE _{H₂} ^c (%)
WO ₃ -DDA	0.89	1.49	65.2	4.46	97.4
WO ₃ -bulk	0.23	0.35	58.1	0.89	74.3

^aFaradic efficiency of O₂ evolution. ^b n_{H_2} is the amount of H₂ evolved in the Pt counter electrode compartment. ^cFaradic efficiency of H₂ evolution.

formation of nanostructure, which generates mesoporosity after removing DDA by calcination. The present surfactant template technique is very unique in terms of use of a solid tungsten precursor in a solvothermal method, compared with a common technique using liquid tungsten precursors for interaction with surfactants in principle. The mesoporous network has a disordered arrangement of pores which is composed of well-connected tiny spherical WO_3 particles with a diameter of *ca.* 5 to 20 nm. The DDA-templated WO_3 photoanode showed three times higher photoanodic current density upon visible light irradiation and provided the efficient performance of PEC water oxidation compared to the untemplated WO_3 , which is promising as an efficient material for high-performance solar energy conversion.

Competing interests

The authors declare that they have no competing interests.

Authors' contributions

LD prepared the samples and performed the photoelectrochemical measurements. DC carried out the analysis and optimization of the results and drafted the manuscript. KS and TY helped analyze the results. MY supervised the data analysis and interpretation of the results and helped draft the manuscript. All authors read and approved the final manuscript.

Acknowledgements

This work was partially supported by the JST PRESTO program and Grant-in-Aid for Scientific Research (B) from the Ministry of Education, Culture, Sports, Science and Technology (No. 24350028). DC thanks JSPS for providing postdoctoral fellowship.

Received: 16 July 2014 Accepted: 11 September 2014

Published: 2 October 2014

References

- Kamat PV, Tvrđy K, Baker DR, Radich JG: Beyond photovoltaics: semiconductor nanoarchitectures for liquid-junction solar cells. *Chem Rev* 2010, **110**:6664.
- Kudo A, Miseki Y: Heterogeneous photocatalyst materials for water splitting. *Chem Soc Rev* 2009, **38**:253.
- Chandra D, Saito K, Yui T, Yagi M: Crystallization of tungsten trioxide having small mesopores: highly efficient photoanode for visible-light-driven water oxidation. *Angew Chem Int Ed* 2013, **52**:12606.
- Kim HG, Borse PH, Jang JS, Ahn CW, Jeong ED, Lee JS: Engineered nanorod perovskite film photocatalysts to harvest visible light. *Adv Mater* 2011, **23**:2088.
- Zukalová M, Zukal A, Kavan L, Nazeeruddin MK, Liska P, Grätzel M: Organized mesoporous TiO_2 films exhibiting greatly enhanced performance in dye-sensitized solar cells. *Nano Lett* 2005, **5**:1789.
- Kim J, Koh JK, Kim B, Kim JH, Kim E: Nanopatterning of mesoporous inorganic oxide films for efficient light harvesting of dye-sensitized solar cells. *Angew Chem Int Ed* 2012, **51**:6864.
- Grätzel M: Photoelectrochemical cells. *Nature* 2001, **414**:338.
- Fujishima A, Honda K: TiO_2 photoelectrochemistry and photocatalysis. *Nature* 1972, **238**:37.
- Aprile C, Corma A, Garcia H: Enhancement of the photocatalytic activity of TiO_2 through spatial structuring and particle size control: from subnanometric to submillimetric length scale. *Phys Chem Chem Phys* 2008, **10**:769.
- Ng KH, Minggu LJ, Kassim MB: Gallium-doped tungsten trioxide thin film photoelectrodes for photoelectrochemical water splitting. *Int J Hydrogen Energy* 2013, **38**:9585.
- Kim JK, Shin K, Cho SM, Lee T-W, Park JH: Synthesis of transparent mesoporous tungsten trioxide films with enhanced photoelectrochemical response: application to unassisted solar water splitting. *Energy Environ Sci* 2011, **4**:1465.
- Chatchai P, Murakami Y, Kishioka S-y, Nosaka AY, Nosaka Y: Efficient photocatalytic activity of water oxidation over $\text{WO}_3/\text{BiVO}_4$ composite under visible light irradiation. *Electrochim Acta* 2009, **54**:1147.
- Hisatomi T, Dotan H, Stefik M, Sivula K, Rothschild A, Grätzel M, Mathews N: Enhancement of the performance of ultrathin hematite photoanode for water splitting by an oxide underlayer. *Adv Mater* 2012, **24**:2699.
- Satsangi VR, Kumari S, Singh AP, Shrivastav R, Dass S: Nanostructured hematite for photoelectrochemical generation of hydrogen. *Int J Hydrogen Energy* 2008, **33**:312.
- Rahman G, Joo O-S: Photoelectrochemical water splitting at nanostructured $\alpha\text{-Fe}_2\text{O}_3$ electrodes. *Int J Hydrogen Energy* 2012, **37**:13989.
- Li Y, Takata T, Cha D, Takanabe K, Minegishi T, Kubota J, Domen K: Vertically aligned Ta_3N_5 nanorod arrays for solar-driven photoelectrochemical water splitting. *Adv Mater* 2013, **25**:125.
- Maeda K, Higashi M, Lu D, Abe R, Domen K: Efficient nonsacrificial water splitting through two-step photoexcitation by visible light using a modified oxynitride as a hydrogen evolution photocatalyst. *J Am Chem Soc* 2010, **132**:5858.
- Maeda K, Domen K: Water oxidation using a particulate $\text{BaZrO}_3\text{-BaTaO}_2\text{N}$ solid-solution photocatalyst that operates under a wide range of visible light. *Angew Chem Int Ed* 2012, **51**:9865.
- Abe T, Nagai K, Kabutomori S, Kaneko M, Tajiri A, Norimatsu T: An organic photoelectrode working in the water phase: visible-light-induced dioxygen evolution by a perylene derivative/cobalt phthalocyanine bilayer. *Angew Chem Int Ed* 2006, **45**:2778.
- Yang B, Zhang Y, Drabarek E, Barnes PRF, Luca V: Enhanced photoelectrochemical activity of sol-gel tungsten trioxide films through textural control. *Chem Mater* 2007, **19**:5664.
- Seabold JA, Choi K-S: Effect of a cobalt-based oxygen evolution catalyst on the stability and the selectivity of photo-oxidation reactions of a WO_3 photoanode. *Chem Mater* 2011, **23**:1105.
- Yagi M, Maruyama S, Sone K, Nagai K, Norimatsu T: Preparation and photoelectrocatalytic activity of a nano-structured WO_3 platelet film. *J Solid State Chem* 2008, **181**:175.
- Miseki Y, Kusama H, Sugihara H, Sayama K: WO_3 photocatalyst showing efficient solar energy conversion for O_2 production and Fe (III) ion reduction under visible light. *J Phys Chem Lett* 2010, **1**:1196.
- Miseki Y, Fujiyoshi S, Gunji T, Sayama K: Photocatalytic water splitting under visible light utilizing I_3^-/I^- and IO_3^-/I^- redox mediators by Z-scheme system using surface treated PtO_x/WO_3 as O_2 evolution photocatalyst. *Catal Sci Tech* 2013, **3**:1750.
- Corma A: From microporous to mesoporous molecular sieve materials and their use in catalysis. *Chem Rev* 1997, **97**:2373.
- Kresge CT, Leonowicz ME, Roth WJ, Vartuli JC, Beck JS: Ordered mesoporous molecular sieves synthesized by a liquid-crystal template mechanism. *Nature* 1992, **359**:710.
- Chandra D, Bekki M, Nakamura M, Sonezaki S, Ohji T, Kato K, Kimura T: Dye-sensitized biosystem sensing using macroporous semiconducting metal oxide films. *J Mater Chem* 2011, **21**:5738.
- Davis ME: Ordered porous materials for emerging applications. *Nature* 2002, **417**:813.
- Sanchez C, Boissière C, Grosso D, Laberty C, Nicole L: Design, synthesis, and properties of inorganic and hybrid thin films having periodically organized nanoporosity. *Chem Mater* 2008, **20**:682.
- Santato C, Ulmann M, Augustynski J: Photoelectrochemical properties of nanostructured tungsten trioxide films. *J Phys Chem B* 2001, **105**:936.
- Santato C, Ulmann M, Augustynski J: Enhanced visible light conversion efficiency using nanocrystalline WO_3 films. *Adv Mater* 2001, **13**:511.
- Santato C, Odziemkowski M, Ulmann M, Augustynski J: Crystallographically oriented mesoporous WO_3 films: synthesis, characterization, and application. *J Am Chem Soc* 2001, **123**:10639.
- Berger S, Tsuchiya H, Ghicov A, Schmuki P: High photocurrent conversion efficiency in self-organized porous WO_3 . *Appl Phys Lett* 2006, **88**:203119.
- Colton RJ, Guzman AM, Rabalais JW: Electrochromism in some thin-film transition-metal oxides characterized by x-ray electron spectroscopy. *J Appl Phys* 1978, **49**:409.
- Yous B, Robin S, Donnadiou A, Dufour G, Maillot C, Roulet H, Senemaud C: Chemical vapor deposition of tungsten oxides: A comparative study by

- X-ray photoelectron spectroscopy, X-ray diffraction and reflection high energy electron diffraction. *Mater Res Bull* 1984, **19**:1349.
36. Sivakumar R, Moses Ezhil Raj A, Subramanian B, Jayachandran M, Trivedi DC, Sanjeeviraja C: Preparation and characterization of spray deposited n-type WO₃ thin films for electrochromic devices. *Mater Res Bull* 2004, **39**:1479.
 37. Saha D, Jensen KMØ, Tyrsted C, Bøjesen ED, Mamakhel AH, Dippel A-C, Christensen M, Iversen BB: In situ total X-ray scattering study of WO₃ nanoparticle formation under hydrothermal conditions. *Angew Chem Int Ed* 2014, **53**:3667.
 38. Wang N, Wang D, Li M, Shi J, Li C: Photoelectrochemical water oxidation on photoanodes fabricated with hexagonal nanoflower and nanoblock WO₃. *Nanoscale* 2014, **6**:2061.
 39. Zeng W, Li Y, Zhang H: Hierarchical WO₃ porous microspheres and their sensing properties. *J Mater Sci: Mater Electron* 2014, **25**:1512.
 40. Katsumata H, Inoue K, Suzuki T, Kaneco S: Facile synthesis of WO₃ nanorod thin film on W substrate with enhanced photocatalytic performance. *Catal Lett* 2014, **144**:837.
 41. Brezesinski T, Fattakhova Rohlffing D, Sallard S, Antonietti M, Smarsly BM: Highly crystalline WO₃ thin films with ordered 3D mesoporosity and improved electrochromic performance. *Small* 2006, **2**:1203.
 42. Sadakane M, Sasaki K, Kunioku H, Ohtani B, Ueda W, Abe R: Preparation of nano-structured crystalline tungsten(vi) oxide and enhanced photocatalytic activity for decomposition of organic compounds under visible light irradiation. *Chem Commun* 2008, 6552.
 43. Chandra D, Yokoi T, Tatsumi T, Bhaumik A: Highly luminescent organic-inorganic hybrid mesoporous silicas containing tunable chemosensor inside the pore wall. *Chem Mater* 2007, **19**:5347.
 44. Grosman A, Ortega C: Capillary condensation in porous materials. Hysteresis and interaction mechanism without pore blocking/percolation process. *Langmuir*. 2008, **24**:3977.

doi:10.1186/1556-276X-9-542

Cite this article as: Li et al.: Unique and facile solvothermal synthesis of mesoporous WO₃ using a solid precursor and a surfactant template as a photoanode for visible-light-driven water oxidation. *Nanoscale Research Letters* 2014 **9**:542.

Submit your manuscript to a SpringerOpen[®] journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Immediate publication on acceptance
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► springeropen.com
