

NANO EXPRESS

Open Access

Influence of the local structure in phase-change materials on their dielectric permittivity

Kostiantyn V Shportko^{1,2*} and Eugen F Venger²

Abstract

Ge-Sb-Te alloys, which belong to the phase-change materials, are promising materials for data storage and display and data visualization applications due to their unique properties. This includes a remarkable difference of their electrical and optical properties in the amorphous and crystalline state. Pronounced change of optical properties for Ge-Sb-Te alloys is linked to the different bonding types and different atomic arrangements in amorphous and crystalline states. The dielectric function of phase-change materials has been investigated in the far infrared (FIR) range. Phonons have been detected by FTIR spectroscopy. Difference of the dispersion of the dielectric permittivity of amorphous and crystalline samples is caused by different structures in different states which contribute to the dielectric permittivity.

Keywords: Phase-change materials; Phonon; Dielectric function

PACS: 70.78.40.F; 70.63.20.K

Background

Ge-Sb-Te alloys are characterized by a profound change of optical and electrical properties between the amorphous and crystalline state, which makes them attractive for data storage [1,2] and display and data visualization [3] applications. The electrical resistivity of the amorphous and crystalline phases commonly differs by about 3 to 4 orders of magnitude, which is very favorable for phase-change memory operation [4].

These properties might be used in memories based on PC materials (PCRAM), which operation relies on the fact that chalcogenide-based materials, such as phase-change alloys that contain Ge, Sb, and Te, can be reversibly switched from an amorphous phase ('0' state) to a crystalline phase ('1' state) or vice versa by an external electric current. PCRAM are a candidate to replace flash memory for non-volatile data storage applications due to their lower power consumption and higher operation speed [5-7].

Phase-change materials have already been employed in optical data storages (CDs, DVDs, Blu-Ray disks) due to

the profound change in the optical properties between the amorphous and the crystalline state. In [3], it was demonstrated that by combining the optical and electronic properties of phase-change materials, display and data visualization applications that go beyond data storage applications can be created. This motivates researchers to investigate and to understand the optical properties of the phase-change materials in a wide spectral range.

Methods

Samples investigated in this study were prepared in a following way: firstly, a 150-nm Al layer was deposited onto a glass substrate. After that, the Ge-Sb-Te film (1,000 nm) was d.c. sputter deposited onto it. In this work, we have investigated two phase-change alloys: Ge₂Sb₂Te₅ and Ge₃Sb₂Te₆. To obtain polycrystalline samples, the as-deposited amorphous films were annealed in Ar atmosphere for 30 min at temperatures about 20°C above their corresponding crystallization temperatures. The structure of the phase-change samples was checked by X-ray diffraction [8]. The phase-change layer thickness was determined on reference samples prepared in the same sputter session using an Alpha-Step 200 profilometer (Tencor Instruments, Milpitas, CA, USA).

* Correspondence: konstantin@shportko.com

¹I. Institute of Physics (IA), RWTH University of Technology Aachen, Sommerfeldstr. 14, Aachen 52056, Germany

²Department of semiconductor heterostructures, V.E. Lashkarev Institute for semiconductor physics of NAS of Ukraine, 45 Nauki av, Kyiv 03028, Ukraine

IR reflectance spectra were measured at room temperature in the range from 50 to 650 cm^{-1} , using a Bruker IFS 66v/s spectrometer with a Hg lamp (Bruker Optics, Ettlingen, Germany) as the radiation source employing a resolution of 1 cm^{-1} . Two hundred fifty-six scans were collected in each experiment. A gold mirror (300 nm thick layer of gold, deposited on glass) with a reflectance of 0.99 in the IR served as a reference for the measurements. To normalize the data, the IR reflectance spectra of the reference and the sample were measured subsequently. After dividing the sample's spectrum by the reference, the final spectrum was obtained. The relative measurement error for the reflectance is 0.2% in the measured wavelength range.

Experimental reflectance spectra were analyzed using the SCOUT software. The model of the dielectric function $\epsilon(\nu)$ used is composed of the following parts: a constant, which is responsible for the polarizability in the higher energy range, a Drude contribution for free charge carriers (in the case of the crystalline samples), and a sum of Kim oscillators to describe the contribution of the IR-active phonons [9,10].

Results and discussion

In the non-phase change covalently bonded semiconductor materials [11,12], the short-range order in the amorphous state is essentially the same as in the crystalline state. This we can illustrate on the example of non-phase-change material AgInTe_2 . Figure 1 presents the dispersion of the dielectric permittivity of AgInTe_2 in the reststrahlen. Curves 1 and 2 correspond to the real and imaginary parts of the dielectric function of the amorphous AgInTe_2 , and curves 3 and 4 are the real and imaginary parts of the dielectric function of the crystalline AgInTe_2 . Both curves 2 and 4 show two phonon peaks at around 136 and 166 cm^{-1} . Peaks of curve 2 are lower and wider, since the amorphous state lacks a

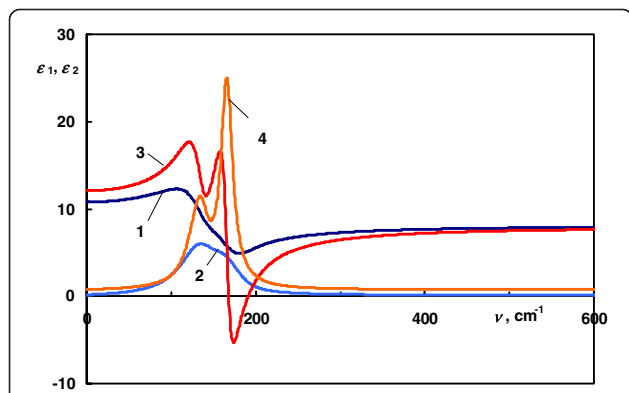


Figure 1 The dispersion of the dielectric permittivity of AgInTe_2 . 1, 2 - ϵ_1 and ϵ_2 of the amorphous sample; 3, 4 - ϵ_1 and ϵ_2 of the crystalline sample.

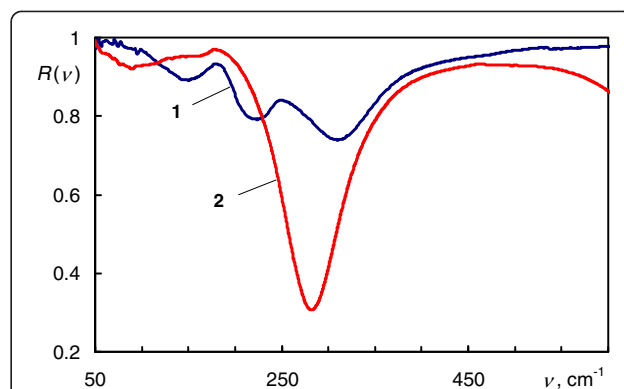


Figure 2 Experimental reflectance spectra of $\text{Ge}_2\text{Sb}_2\text{Te}_5$. 1 - amorphous, 2 - crystalline.

long-range order of crystalline state. The peaks are placed almost at the same wavenumbers as those in curve 4, because the amorphous state has the same local arrangement as crystal. Short-range order is controlled by a chemical bond, and for AgInTe_2 , it does not change upon transition between amorphous and crystalline state; therefore, $\epsilon_{1\text{amorphous}} \approx \epsilon_{1\text{crystalline}}$ (above 400 cm^{-1}).

The amorphous state of phase-change materials is bonded covalently, while the crystalline phase utilizes resonant bonding. Due to this fact, the dielectric permittivity of the crystalline phase above the reststrahlen and below the optical band gap is several times bigger than that of the amorphous phase [13]. Vibrational properties of phase-change materials have been studied using Raman spectroscopy in [14-16]. In this study, we have focused on the dispersion of dielectric function of phase-change materials in the reststrahlen. The dielectric function of two Ge-Sb-Te alloys: $\text{Ge}_2\text{Sb}_2\text{Te}_5$ and $\text{Ge}_3\text{Sb}_2\text{Te}_6$, has been investigated.

Optical contrast in the IR reflectance spectra of Ge-Sb-Te alloys has been observed in the far infrared (FIR).

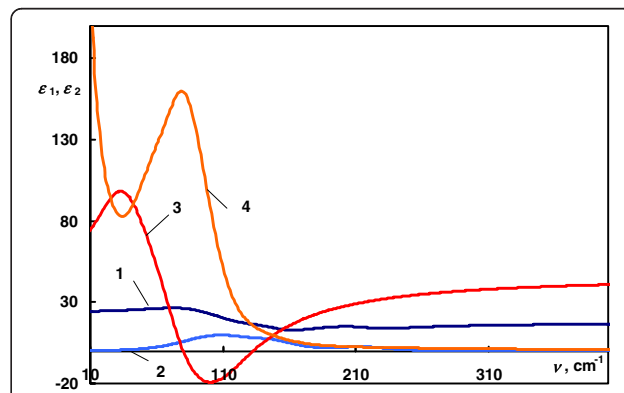


Figure 3 The dispersion of the dielectric permittivity of $\text{Ge}_2\text{Sb}_2\text{Te}_5$. 1, 2 - ϵ_1 and ϵ_2 of the amorphous sample; 3, 4 - ϵ_1 and ϵ_2 of the crystalline sample.

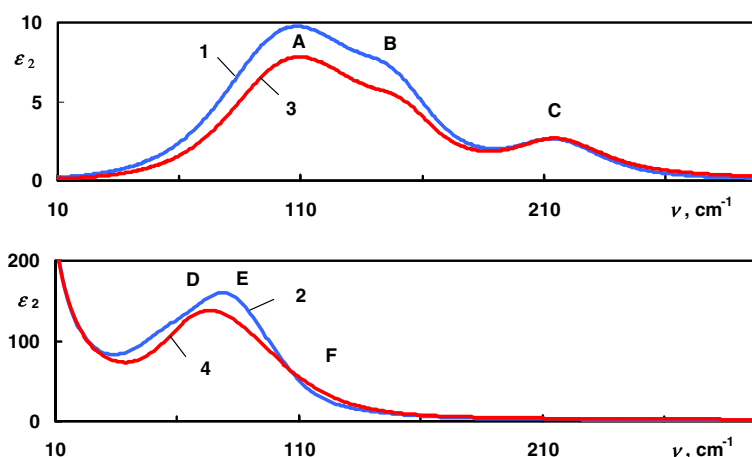


Figure 4 The dispersion of the imaginary part of the dielectric permittivity of Ge-Sb-Te alloys. Ge₂Sb₂Te₅: 1 - amorphous, 2 - crystalline; Ge₃Sb₂Te₆: 3 - amorphous, 4 - crystalline.

Experimental reflectance spectra of Ge₂Sb₂Te₅ are shown in Figure 2. Two deep minima above 250 cm⁻¹ in curves 1 and 2 are caused by the interference of the IR light in the Ge₂Sb₂Te₅ film, other minima correspond to the phonons' absorption.

The dispersion of the dielectric function of amorphous and crystalline Ge₂Sb₂Te₅ was obtained from the fit of IR reflectance spectra, and it is shown in the Figure 3. Curves 1 and 2 correspond to the real and imaginary parts of the dielectric function of the amorphous Ge₂Sb₂Te₅, and curves 3 and 4 are the real and imaginary parts of the dielectric function of the crystalline Ge₂Sb₂Te₅. Unlike non-phase-change AgInTe₂, one can notice the profound difference between the dielectric function of amorphous and crystalline phase-change Ge₂Sb₂Te₅. On one hand, $\epsilon_{2\text{amorphous}}(\nu)$ has following peaks at around 115 cm⁻¹, 'shoulder' 149 cm⁻¹, and small peak at 217 cm⁻¹. On other hand, $\epsilon_{2\text{crystalline}}(\nu)$ shows rise at very low wavenumbers; this corresponds to the contribution of free charge carriers and one strong phonon peak near 80 cm⁻¹ with a wide slope above 100 cm⁻¹. Due to the high electronic polarizability in the crystalline state of Ge₂Sb₂Te₅, $\epsilon_{1\text{crystalline}} > \epsilon_{1\text{amorphous}}$ in the range above 250 cm⁻¹. The dispersion of the dielectric function of Ge₃Sb₂Te₆ has almost the same appearance in the FIR. Real and imaginary parts of the dielectric function of both alloys have been obtained from the fit of experimental reflectance spectra and are shown in Figure 4. The dielectric function of amorphous Ge-Sb-Te alloys in the FIR has been composed of three oscillators; in the case of crystalline Ge-Sb-Te alloys, 3 oscillators and Drude component were used. Corresponding positions of the phonons' absorption peaks (in cm⁻¹) in the $\epsilon_2(\nu)$ of studied Ge-Sb-Te alloys are shown in Table 1.

In Ge-Sb-Te alloys, the Ge and Te atoms build the octahedral and tetrahedral structures. A. Kolobov et al. [17] claim that the Ge atoms occupy the octahedral and tetrahedral symmetry positions in the crystalline and amorphous states in Ge-Sb-Te alloys, respectively. Authors [18] have reported the phonon energies in Ge-Sb-Te alloys and assigned them to the vibrations of the structures built from the Ge and Te atoms.

To explain the contrast in the dispersion of the dielectric function between amorphous and crystalline Ge-Sb-Te samples, we compared our experimental results with data from [18]. According to [18], we assigned oscillators used to model the dielectric function of Ge₂Sb₂Te₅ and Ge₃Sb₂Te₆ (Table 1) to the vibrations of Ge-Te octahedra and tetrahedra. In amorphous Ge-Sb-Te, peaks A and B are close to the energies of the vibrations of Ge-Te octahedra; the peak C corresponds to the vibrations of Ge-Te tetrahedra. In case of crystalline Ge-Sb-Te alloys, peaks D, E, and F correspond to the vibrations of Ge-Te octahedra.

Table 1 Positions of the phonons' absorption peaks (in cm⁻¹) in the $\epsilon_2(\nu)$ of studied Ge-Sb-Te alloys

Peak	Ge ₂ Sb ₂ Te ₅	Ge ₃ Sb ₂ Te ₆
Amorphous		
A	115	116
B	149	150
C	217	216
Crystalline		
D	69	74
E	89	91
F	135	133

Conclusions

The contrast of the dielectric function of amorphous and crystalline phase-change materials has been observed in the FIR. In this range, the dielectric function is mainly governed by the phonons, and it was modeled by the sum of oscillators, which were attributed to the vibrations of Ge-Te octahedra and tetrahedra. Observed contrast of optical properties of phase-change materials in the FIR is caused by different contributions of the local structures into the dielectric permittivity of Ge-Sb-Te alloys.

Competing interests

The authors declare that they have no competing interests.

Authors' contributions

KS performed the measurements and drafted the manuscript. KS and EV discussed the results. EV helped to draft the manuscript. Both authors read and approved the final manuscript.

Acknowledgements

One of the authors (K. Shportko) gratefully acknowledges the support from the DAAD (German Academic Exchange Service) and the SFB 917 'Resistively Switching Chalcogenides for Future Electronics - Structure, Kinetics and Device Scalability'.

Received: 19 October 2014 Accepted: 6 January 2015

Published online: 05 February 2015

References

- Ovshinsky SR. Reversible electrical switching phenomena in disordered structures. *Phys Rev Lett.* 1968;21:1450–6.
- Wuttig M, Yamada N. Phase-change materials for rewriteable data storage. *Nat Mater.* 2007;6:824–32.
- Hosseini P, Wright CD, Bhaskaran H. An optoelectronic framework enabled by low-dimensional phase-change films. *Nature.* 2014;511:206–12.
- Friedrich I, Weidenhof V, Njoroge W, Franz P, Wuttig M. Structural transformations of Ge₂Sb₂Te₅ films studied by electrical resistance measurements. *J Appl Phys.* 2000;87:4130–4.
- Kang D, Ahn D, Kim K, Webb JF, Yi K. One-dimensional heat conduction model for an electrical phase change random access memory device with an 8F2 memory cell F = 0.15 mkm. *J App Phys.* 2003;94:3536–42.
- Hosaka S, Miyauchi K, Tamura T, Yin Y, Sone H. Prototype of phase-change channel transistor for both nonvolatile memory and current control. *IEEE Trans Electron Dev.* 2007;54:517–24.
- Karpov VG, Kryukov YA, Savransky SD, Karpov IV. Nucleation switching in phase change memory. *Appl Phys Lett.* 2007;90(1–3):123504.
- Shpotyuk O, Calvez L, Petracovschi E, Klym H, Ingram A, Demchenko P. Thermally-induced crystallization behaviour of 80GeSe₂–20Ga₂Se₃ glass as probed by combined X-ray diffraction and PAL spectroscopy. *J Alloy Comp.* 2014;582:323–7.
- Fox M. *Optical properties of solids.* New York: Oxford University Press; 2001.
- Uhanov YI. *Optical properties of semiconductors.* Moscow: Nauka; 1977.
- Shportko KV, Pasechnik Yu A, Wuttig M, Rueckamp R, Trukhan VM, Haliakovich TV. Plasmon–phonon contribution in the permittivity of ZnP₂ single crystals in FIR at low temperatures. *J Vibr Spectr.* 2009;50:209–13.
- Shportko KV, Izotov AD, Trukhan VM, Shelkovaya TV, Venger EF. Effect of temperature on the region of residual rays of CdP₂ and ZnP₂ single crystals. *Russ J Inorg Chem.* 2014;59:986–91.
- Shportko K, Kremers S, Woda M, Lencer D, Robertson J, Wuttig M. Resonant bonding in crystalline phase-change materials. *Nat Mater.* 2008;7:653–8.
- Mazzarello R, Caravati S, Angioletti-Uberti S, Bernasconi M, Parrinello M. Signature of tetrahedral Ge in the Raman spectrum of amorphous phase-change materials. *Phys Rev Lett.* 2010;104(1–4):085503.
- Sosso GC, Caravati S, Gatti C, Assoni S, Bernasconi M. Vibrational properties of hexagonal Ge₂Sb₂Te₅ from first principles. *J Phys Condens Matter.* 2009;21(1–8):245401.
- Sosso GC, Caravati S, Mazzarello R, Bernasconi M. Raman spectra of cubic and amorphous Ge₂Sb₂Te₅ from first principles. *Phys Rev B.* 2011;83(1–8):134201.
- Kolobov AV, Fons P, Frenkel AI, Ankudinov AL, Tominaga J, Uruga T. Understanding the phase-change mechanism of rewritable optical media. *Nat Mater.* 2004;3:703–8.
- Matsunaga T, Yamada N, Kojima R, Shamoto S, Sato M, Tanida H, et al. Phase-change materials: vibrational softening upon crystallization and its impact on thermal properties. *Adv Funct Mater.* 2011;20:1–8.

Submit your manuscript to a SpringerOpen[®] journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Immediate publication on acceptance
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► springeropen.com