

NANO EXPRESS

Open Access



Sol-gel Synthesis, Photo- and Electrocatalytic Properties of Mesoporous TiO₂ Modified with Transition Metal Ions

N. Smirnova^{1*} , I. Petrik¹, V. Vorobets², G. Kolbasov² and A. Eremenko¹

Abstract

Mesoporous nanosized titania films modified with Co²⁺, Ni²⁺, Mn³⁺, and Cu²⁺ ions have been produced by templated sol-gel method and characterized by optical spectroscopy, X-ray diffraction (XRD), and Brunauer, Emmett, and Teller (BET) surface area measurement. Band gap energy and the position of flat band potentials were estimated by photoelectrochemical measurements. The films doped with transition metals possessed higher photocurrent quantum yield, as well as photo- and electrochemical activity compared to undoped samples. Mⁿ⁺/TiO₂ (M=Co, Ni, Mn, Cu) electrodes with low dopant content demonstrate high efficiency in electrocatalytic reduction of dissolved oxygen. Polarization curves of TiO₂, TiO₂/Ni²⁺, TiO₂/Co^{2+/3+}, and TiO₂/Mn³⁺ electrodes contain only one current wave (oxygen reduction current). It means that reaction proceeds without the formation of an intermediate product H₂O₂.

Keywords: Mesoporous TiO₂, Nanosized films, Doping with transition metal ions, Cr^{VI} photoreduction, Electrocatalytic oxygen reduction

PACS: 82.45.Mp, 82.45.-h, 82.50.Hp

Background

Among the semiconductor materials, titanium dioxide attracts the great attention because of its chemical stability, biological inertness, low toxicity, and relatively low cost. TiO₂ is a promising material for application in environmental photocatalysis, for the generation of electricity in the solar and fuel cells, gas sensors, optical and protective coatings, electrochemical devices, etc. [1, 2]. Nowadays, the efforts of researchers are directed on the selection of modifiers that would expand the functionality of TiO₂ coatings without reducing their photocatalytic activity. For example, transition metals such as Co, Ni, and Mn are well known as magnetic materials, copper and many of its compounds have antibacterial properties. As was reported by D. Banneman [3], modification of TiO₂ nanoparticles with d-metals having an unpaired electron leads to increase the photocatalytic activity. Doping with

Co, Ni, and Mn ions increases the photocatalytic activity of TiO₂ powders and changes magnetic properties of such materials [4]. The copper ion's ability to increase the photocatalytic activity of titanium dioxide under UV irradiation in reaction of metallic copper deposition, decomposition of formic acid, cyanide and cyanate [5, 6] connected with the efficient capturing the electrons of the TiO₂ conduction band on Cu²⁺ and Cu⁺ energy levels near conductive band in the band gap of TiO₂. The increase of catalytic activity in photooxidation reactions can occur in the presence of Cu²⁺ ions through more efficient formation of H₂O₂ and active OH[•] radicals [7]. At the same time, decrease of the photoactivity of Mⁿ⁺-TiO₂ materials prepared by ion beam-induced CVD in comparison with TiO₂ was reported in [8].

Compared with industrial production [6], the sol-gel synthesis is a simple, relatively inexpensive, and reliable method for receiving of mesoporous materials [9, 10] that achieves high chemical homogeneity of formed products with significant decrease of the heating temperature and duration of heat treatment. This is a

* Correspondence: smirnat@i.ua

¹O.Chuiko Institute of Surface Chemistry, Ukrainian National Academy of Sciences, 17 General Naumov Street, Kyiv 03680, Ukraine
Full list of author information is available at the end of the article

promising approach for the synthesis of powders and films of individual oxides [11] and mixed oxide materials [12, 13], production of nanostructured TiO₂ doped with nanoparticles of noble metals [14], or transition metal oxides, due to a number of its advantages: the possibility of controlling the size of the crystals and the phase composition, the production of transition crystal structures, and the formation of high surface area.

In this paper, template sol-gel synthesis of mesoporous titanium dioxide films modified with transition metal ions (cobalt, nickel, manganese, and copper) is reported. Phase composition, optical properties, and energy parameters (band gap E_g and flat band potential E_{fb}) of the resulting materials are investigated. The aim of this work is to study the effect of 3d-metal dopants in TiO₂ films on their photo- and electrocatalytic properties on the example of the photoreduction reaction of potassium dichromate under UV irradiation and electroreduction of oxygen, which is the basis of electrochemical sensors of O₂, that today are widely used to determine the concentration of dissolved oxygen as in industrial processes and in medical practice.

Methods

Mesoporous TiO₂, Coⁿ⁺/TiO₂, Niⁿ⁺/TiO₂, Mnⁿ⁺/TiO₂, and Cuⁿ⁺/TiO₂ films and powders were synthesized via templated sol-gel method according to [14] using Ti(OiPr)₄, CuSO₄·5H₂O, Co(CH₃COO)₂·4H₂O, Ni(HCOO)₂·2H₂O, MnCl₂·4H₂O as titania and 3d-metal sources, Pluronic P123 as template, and acetylacetone as complexing agent. The molar ratios of the components were as follows: Pluronic P123:acetylacetone:HNO₃:Ti(OiPr)₄ = 0.1:1:2:2. For film deposition onto glass or titanium substrates, dip-coating technique was utilized. After deposition of the film, gelation, and gel ripening, it was dried in air at room temperature for 2 h. The dried films were sintered at 400 °C. At this temperature, the ordered porous structure of the oxide film is formed. To facilitate structural investigations by X-ray diffraction (XRD), corresponding powders have been prepared via gelation of the films' precursors, their drying in air with following heat treatment at 450 or 650 °C. XRD measurements were performed using a DRON-4-07 (Burevestnik, St. Petersburg) diffractometer (CuK α radiation with Ni filter) with Bragg-Brentano registration geometry ($2\theta = 10\text{--}60^\circ$). The average size of crystallites was determined using Scherrer equation applied to the most intensive peak. The degree of the powder crystallinity was estimated as the ratio of integrated intensities, such as for the (101) line of the studied and reference standard samples (reference standard: TiO₂, anatase 100%). Optical spectra of the films and powders were recorded using a Perkin-Elmer Lambda Bio 35 UV-Vis with integrating sphere Labsphere RSA-PR-20 in spectral diapason 200–1000 nm. The film thickness and refractive

index were measured using a multi-angle ellipsometer LEF-3M ($\lambda = 632.8$ nm).

Photoelectrochemical investigations of the TiO₂ and Mⁿ⁺/TiO₂ electrodes were carried out in the wavelength range 250–600 nm in a quartz electrochemical cell under irradiation of a high-pressure xenon lamp, which gave light with a frequency of 20 Hz passing through a monochromator with spectral resolution of 1 nm and focused on the semiconductor electrode. The i_{ph} spectra were expressed in units of quantum efficiency (electron/photon). Ag/AgCl electrode was used as the reference electrode on the pH value of the electrolyte. Electrocatalytic activity of Mⁿ⁺/TiO₂ films in the process of oxygen reduction was studied by means of the current-voltage dependencies measured in potentiodynamic mode using a specially designed electrochemical stand with the following characteristics: measured currents $2 \times 10^{-9} \div 10^{-1}$ A, speed of the potential sweep 0.01 \div 50 mV/s, and the working range $-4 \div +4$ V.

Photocatalytic activity of the synthesized films has been checked in the process of Cr(VI) to Cr(III) photoreduction in water solution of K₂Cr₂O₇ ($C_M = 2 \times 10^{-4}$ M) in the presence of electron donor EDTA ($C_M = 2 \times 10^{-4}$ M) at pH = 2. The open reactor with the reaction components (enabled continues inflow of oxygen) was irradiated with an UV light of mercury lamp PRK-1000 with $P_0 = 3 \times 10^{-7}$ einstein dm⁻³ s⁻¹ intensity. Running water was circulated through the jacket to ensure constant temperature of the magnetically stirred reaction mixture. During the experiments, concentration of reagents has been controlled with an UV-VIS spectrometer Perkin-Elmer Lambda-35.

Results and Discussion

Crystalline Structure of Mⁿ⁺/TiO₂ Nanocomposites

The diffraction reflex at low $2\theta = 2$ values in the diffraction patterns of the initial films and powders correspond to the ordered mesostructures formed by the template Pluronic. The absence of this reflex in the diffraction patterns of calcined powders indicates the disordering of organized structure in the process of crystallization of titanium dioxide. Investigation of the adsorption-desorption isotherms of nitrogen at -196 °C and the pore size distribution for the powders calcined at 450 °C showed that the mesoporous structure with an average pore size of 2.5–6 nm with specific surface area (S_{BET}) from 147 (pure TiO₂) to 224 m²/g for manganese samples was formed. Increasing the concentration of dopant ions from 1 to 5% insignificantly influenced on S_{BET} .

The diffraction peaks in the XRD patterns of films calcined at 450 °C (Fig. 1a) can be attributed to the anatase [ID = 71–1168]. The average size of crystallites was determined using Scherrer equation applied to the most intensive peak (101) of anatase using the Scherrer formula. For TiO₂ film, it was 8 nm, while for Co/TiO₂,

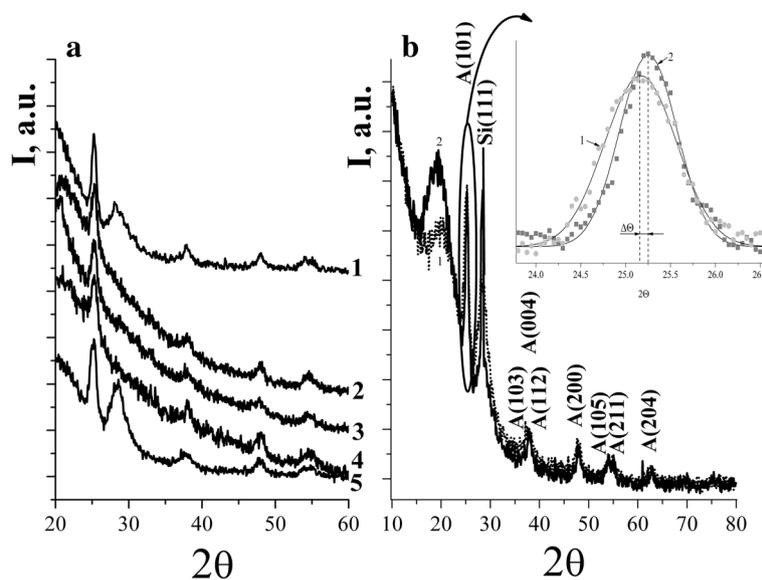


Fig. 1 **a** XRD pattern of TiO₂ (1), Co/TiO₂ (2), Ni/TiO₂ (3), Mn/TiO₂ (4), and Cu/TiO₂ (5) films doped with 5% of metal ions. **b** XRD patterns of TiO₂ (1), Cu/TiO₂ (5.5% Cu) (2) films and Gauss deconvolution of (101) peak (inset)

Ni/TiO₂, Mn/TiO₂, and Cu/TiO₂ (5% of dopant)—14, 14, 15, and 15 nm, respectively. Thus, the addition of transition metal ions in the precursor films of TiO₂ accelerates crystallization and contributes to the growth of crystals, similar to results [15]. Similarity in the Ti⁴⁺, Ni²⁺, Co²⁺, Mn³⁺, and Cu²⁺ ionic radii (68, 69, 72, 80, and 72 pm, respectively) allows the interstitial incorporation of the dopant ions into the anatase lattice [15, 16]. In the case of copper-containing films, such inclusion leads to a shift in the peak of 101 in diffraction pattern (Fig. 1b).

Figure 2a, b presented the structure of powders obtained from precursors of films that were calcined to 450 °C (a) and 650 °C (b). CoTiO₃, NiTiO₃, and Mn₂O₃ were detected in the XRD patterns of 5% Co/TiO₂, Ni/TiO₂, and Mn/TiO₂ powders, respectively, when annealing temperature increased up to 650 °C. There were no displacements of the peaks of anatase or rutile in the XRD patterns of these powders, as it was observed for Cu/TiO₂ films (≤5% Cu). Low-intensity phase reflexes of CuO, Cu₂TiO₃, and Cu₃TiO₄ for copper-containing systems were registered only at concentrations of Cu²⁺ ≥ 15%.

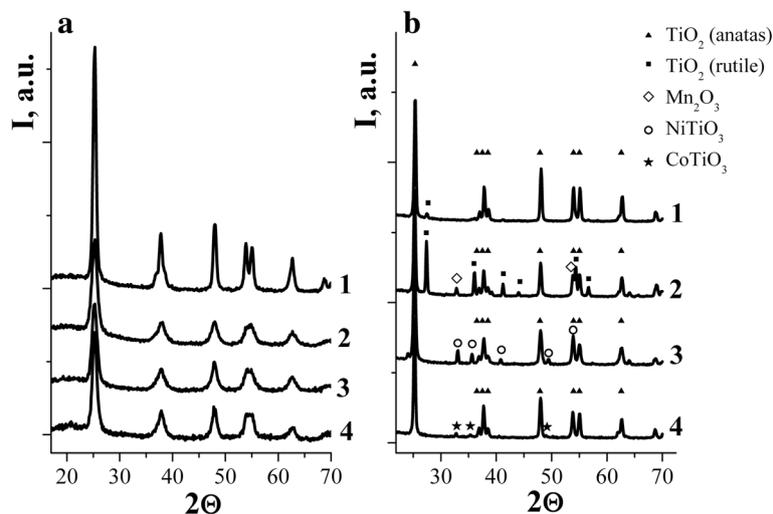


Fig. 2 XRD patterns of Cu/TiO₂ (1), Mn/TiO₂ (2), Ni/TiO₂ (3), and Co/TiO₂ (4) powders doped with 5% of metal ions calcined at 450 (a) and 650 °C (b)

The presence of rutile phase was observed only in the samples of 5% Cu/TiO₂ and 5% Mn/TiO₂. The authors [17] have previously shown that the doping with manganese ions reduced the temperature of anatase-rutile phase transition. Concentration of rutile to the anatase in powder 5% Cu/TiO₂ is negligible while in the manganese sample it was 41%.


Optical Properties of Films and Powders Mⁿ⁺/TiO₂

Obtained films were transparent, robust, and homogeneous. The refractive index and thickness of the films were measured by ellipsometry method. TiO₂ film's refractive index was 1.87 (2.55—for the bulk material), and the thickness was 64 nm. The smaller value of the refractive index of the films is due to the contribution of air ($n = 1$) to the developed pore structure in the effective refractive index of TiO₂-air [18]. The refractive indexes of the films with Cu content of 5 and 20% are 1.94 and 1.66, and the thicknesses are 60 and 50 nm, respectively. The refractive indexes of the films containing 5% Co, 5% Mn, and 5% Ni were 1.92, 1.87, and 1.88, and the thicknesses were 95, 100, and 108 nm, respectively. Change of the thickness of the films can be attributed to a slight change in viscosity of the solution by adding an aqueous solution of salts of transition metals, as well as particularity of structure formation during annealing of the films. The absorption band in the UV region ($\lambda = 380$ nm) of diffuse reflectance spectra of the Mⁿ⁺/TiO₂ powders after heat treatment at 450 °C (Fig. 3a) can be attributed to the band gap excitation of anatase TiO₂ which corresponds to the band to band transition from Ti 3d to O 2p levels. [19]. There is a significant bathochromic shift of the absorption edge for all powders doped with transition metal ions. When transition metal ions incorporated into the lattice, the dopant level appeared between the valence band and the conduction band of TiO₂, thus altering the band-gap energy and shift the absorbance edge to the visible light

region [20]. There are the formation of additional energy levels in the band gap of TiO₂ and decrease the E_g value induced by transition metal ions [20, 21, 22]. Such energy changes in a number of cases (at low concentrations of dopants) can increase the sensitivity of the photocatalyst in the visible region of the spectrum [19].

In the diffuse reflectance spectra of cobalt-containing powders of titanium dioxide absorption bands in the region of 650–800 nm (Co²⁺_{Td}), 450–550 nm (Co²⁺_{Oh}), and 350–440 nm (Co³⁺_{Oh}), corresponding to d-d transitions in ions of cobalt of octahedral and tetrahedral coordination [21, 22] was observed (Fig. 3a, b curve 2). The absorption band at 350–440 nm is overlapped with the fundamental absorption band of titanium dioxide. According to [23], the presence of a band at 600–670 nm (Co²⁺_{Td}), along with the characteristic absorption bands of Co²⁺_{Oh} and Co³⁺_{Oh}, indicates the presence of spinel Co₃O₄ in samples. This d-transition is characterized by a high extinction which allows selecting a state of cobalt among others, even if it is a small amount [23].

According to [24], there are three allowed spin transitions from ³A_{2g} to ³T_{2g}, ³T_{1g}, ³T_{1g}(P) that are located in the range of 770–1430, 500–910, and 370–525 nm for the systems of six-coordinated octahedral nickel (II). The state corresponding to forbidden spin transition to ¹E_g lies close to the ³T_{1g}, so their considerable mixing occurs. Therefore, the doublet band is observed in the spectrum. The optical spectra of Ni²⁺ is characterized by absorption at 410 and 730 nm, which correspond to nickel ions in octahedral environment (Ni²⁺_{Oh}), and absorption at 525 and 650 nm, corresponding to Ni²⁺ ions in tetrahedral environment (Ni²⁺_{Td}) [25]. The absorption band of Ni²⁺_{Oh}, lying at 400–450 nm, is hard to distinguish from the fundamental absorption band of titanium dioxide (Fig. 3a, b curve 3). However, for the samples annealed at 650 °C, there is a distinct band with a maximum at 450 nm and a doublet at 750–850 nm. Three main characteristic absorption bands for nickel oxide

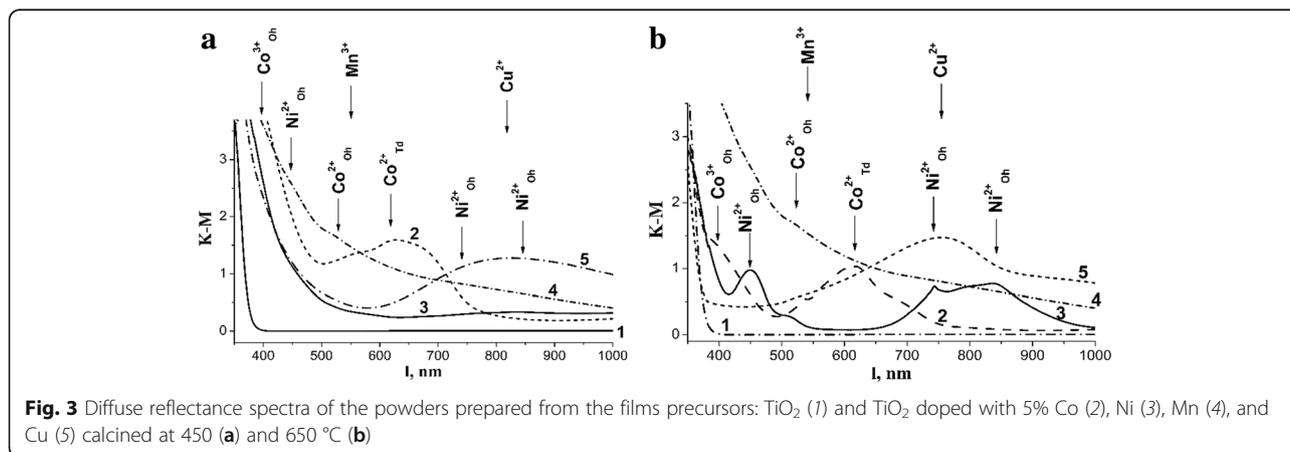

(NiO) are observed at 407, 671, and 741 nm [24]. In the diffuse reflectance spectra of sample 5% Ni/TiO₂ (650 °C), these bands are shifted to longer wavelengths (450, 743, and 837 nm, respectively), probably due to the distortion of the octahedral environment during the formation of nickel titanate (Fig. 3b).

The increase of Mn concentration in manganese-containing samples up to 5% (Fig. 3a, b curve 4) led to appearance of the shoulder at 550 nm in the diffuse reflectance spectra that corresponds to the transition in Mn³⁺ ions in an octahedral environment ${}^5E_g \rightarrow {}^5T_{2g}$ [19, 21]. Characteristic absorption bands of Mn²⁺_{Oh} and Mn⁴⁺_{Oh} [24, 26] in the short-wavelength region (450 nm) are overlapped with the fundamental absorption bands of titanium dioxide.

The broad structureless absorption band with a maximum at 800 nm was observed in the diffuse reflectance spectra of powders of Cu²⁺/TiO₂. The absorption in the spectral region 600–1100 nm may be indicative for the existence of the copper (II) with a tetrahedral structure or a similar distorted structure (Fig. 3a, b curve 5) It is known that divalent copper ions have the electron configuration of 3d⁹. Ions with d⁹ configuration as a rule exhibit the stoichiometric mobility. Only one term ²D belongs to this configuration, which splits into two terms ²T₂ and ²E in a cubic field. In a tetrahedral field, the lower level is the first term and in the octahedral—the second term. The observed peak can be attributed to the ${}^2E_g \rightarrow {}^2T_{2g}$ transition [19, 22, 27].

Photoelectrochemical Characterization and Electrocatalytic Activity of Mⁿ⁺/TiO₂ Films

Spectral dependences of photocurrent were measured for the TiO₂ and Mⁿ⁺/TiO₂ electrodes produced via coating of Mⁿ⁺/TiO₂ films on Ti substrate (Fig. 4) to obtain the value

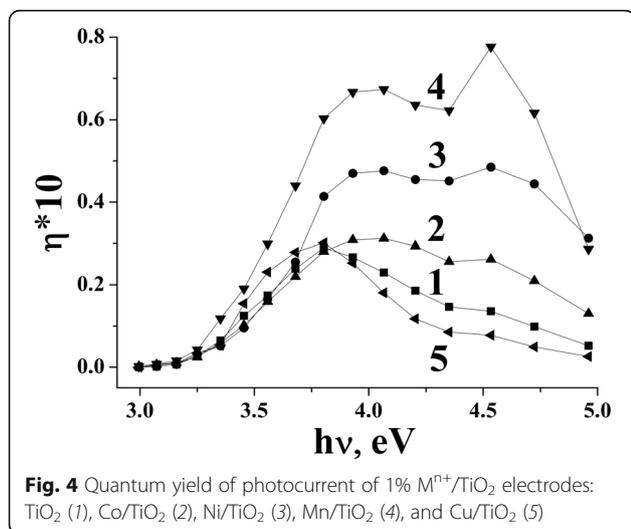


Fig. 4 Quantum yield of photocurrent of 1% Mⁿ⁺/TiO₂ electrodes: TiO₂ (1), Co/TiO₂ (2), Ni/TiO₂ (3), Mn/TiO₂ (4), and Cu/TiO₂ (5)

of the band-gap energy. Photocurrent quantum yield for all of 1% M/TiO₂ films is higher than that for undoped TiO₂.

The enhancement of photocurrent efficiency indicated that Mⁿ⁺ ion addition is beneficial to promote charge separation within nanostructured TiO₂ film and to improve interfacial charge transfer process due to formation of impurity electron levels of 3d metals in the band gap of titanium dioxide [21, 28, 29], acting as traps of charge which retard the recombination process. It is well known that quantum yield of photoelectrochemical current η in semiconductors can be expressed as [30]:

$$\eta = \frac{A}{hv} (hv - E_g)^m$$

where hv is the photon energy, $m = 1/2$ for the direct transition, and $m = 2$ for the indirect transition. For the tested Mⁿ⁺/TiO₂ compositions, photocurrent spectra were presented as $(\eta \times hv)^{1/2} = f(hv)$ dependence which was linear in the wide range of wavelength. Experimental data fit better to an indirect transition. Band gap (E_g) values were calculated [31, 32] by extrapolation of straight line of these dependences to the abscissa (Table 1). E_g values obtained by this method are located in the range of 2.88–3.09 eV (Table 1). For M/TiO₂ films, the E_g values decrease with the increase of dopant content. That is probably associated with the formation of new phases. To test whether the narrower band gap is caused by a shift of the valence (E_{vb}) or conduction band (E_{cb}) edges, the position of the flat band potential (E_{fb}) of the catalysts was determined by the direct electrochemical measurements of photocurrent as a function of applied potential in aqueous 0.5 NaCl. Flat band potentials were estimated from i_{ph} changes measured at the photocurrent maximum for TiO₂ and Mⁿ⁺/TiO₂ films coated on to titanium substrate in aqueous 0.5 M NaCl plotted against applied potential by extrapolation straight line of these

Table 1 Photoelectrochemical characterization of M/TiO₂ films (M—Co, Ni, Mn, Cu)

Sample	E_{fb} (eV) vs NHE	Quantum yield of photocurrent η (a.u.)	E_g (eV)	$E_{1/2}$ (V)
TiO ₂	−0.42	1	3.09	−0.58
1% Ni/TiO ₂	−0.42	1.66	3.07	−0.46
5% Ni/TiO ₂	−0.45	1.14	2.95	−0.76
1% Co/TiO ₂	−0.36	1.07	3.07	−0.52
5% Co/TiO ₂	−0.80	0.28	2.97	−0.67
1% Mn/TiO ₂	−0.48	2.80	3.08	−0.52
5% Mn/TiO ₂	−0.40	0.93	2.88	−0.6
1% Cu/TiO ₂	−0.30	1.03	3.08	−0.55
5% Cu/TiO ₂	−0.15	1.14	3.07	−0.78
30% Cu/TiO ₂	−0.10	0.94	2.99	

dependences to the abscissa. Flat band potential values (Table 1) for the TiO_2 differ insignificantly and are comparable with the value from -0.47 to -0.49 V vs NHE, obtained at $\text{pH} \approx 7$ for nitrogen-doped titanium dioxide [33] and $E_{\text{fb}} = -0.58$ V measured for anatase single crystal [34].

As followed from Table 1, increase of $\text{M}^{\text{n+}}$ content leads to the cathodic shift of the bottom of the conduction band ΔE_{cb} along with E_{g} decrease. The most significant changes of flat band potential values were observed for Cu-doped samples and 5% Co/ TiO_2 that probably related with coexistence of two valence states of dopant ions. As the location of the conduction band is a measure of the reduction power of the photogenerated electrons, we can predict the enhancing of catalytic activity in photoreduction processes.

The oxygen electroreduction process was investigated in physiological (0.9%) solutions of NaCl. It has been found that oxygen reduction polarization curves of TiO_2 electrodes doped with Co (1–5%), Ni (1–5%), Mn (1–5%), and Cu (1–5%) exhibited only one polarographic current wave at potentials of -0.40 to -0.9 V (against silver-chloride reference electrode) (Fig. 5). This suggests that the reaction proceeds without the formation of intermediate H_2O_2 [35, 36], the number of electrons involved in the electroreduction of oxygen on the $\text{M}^{\text{n+}}/\text{TiO}_2$ electrodes, is 2. For $\text{TiO}_2/\text{Mn}^{3+}$ (1%) sample, the polarization curves have not clearly defined threshold current (Fig. 5b, curve 1) but with the further potential cycling, their shape changes and takes the form characteristic of polarization curves for TiO_2 with the limiting current -0.65 – -0.95 V (against silver-chloride reference electrode) (Fig. 5, curve 2).

The mechanism of oxygen reduction on the electrodes under investigation is determined by mixed kinetics. We

have shown that the limiting oxygen reduction current for the semiconductor electrodes is diffusion current, the dependence of limiting current on dissolved oxygen concentration being linear.

The introduction of small amounts of a dopant ($\sim 1\%$) in the TiO_2 film leads to an increase of catalytic activity, which manifests itself in the reduction half-wave reduction potential of O_2 compared to unmodified samples. At a higher dopant content ($>5\%$), the decreasing of catalytic activity for all 3d metals was observed, half-wave potential of oxygen reduction shifted in the cathodic region compared with TiO_2 electrodes.

Photocatalytic Activity of $\text{M}^{\text{n+}}/\text{TiO}_2$ Films

Photocatalytic activity of TiO_2 and $\text{TiO}_2/\text{Cu}^{2+}$, $\text{TiO}_2/\text{Co}^{2+}$, $\text{TiO}_2/\text{Mn}^{3+}$, and $\text{TiO}_2/\text{Ni}^{2+}$ films has been tested in the photoreduction of toxic Cr(VI) to non-toxic Cr(III) ions in acid water solutions in the presence of environmentally important substrate EDTA as electron acceptor. This process has been taken as a model of real wastewaters, where oxidants and reductants are present together, for comparable studies of commercial samples and Pt/ TiO_2 powders [32]. The mechanism of photocatalytic Cr(VI) reduction in the presence of electron scavenger is well described in [37, 38]. Under irradiation in the presence of $\text{M}^{\text{n+}}/\text{TiO}_2$ films, the changes in Cr(VI) concentration was followed by decrease of absorption band intensity at 349 nm, simultaneously the absorption at 550 nm increases due to non-toxic Cr(III) formation. Dependence of Cr(VI) to Cr(III) first order rate constants on of the dopant concentration presented in Table 2.

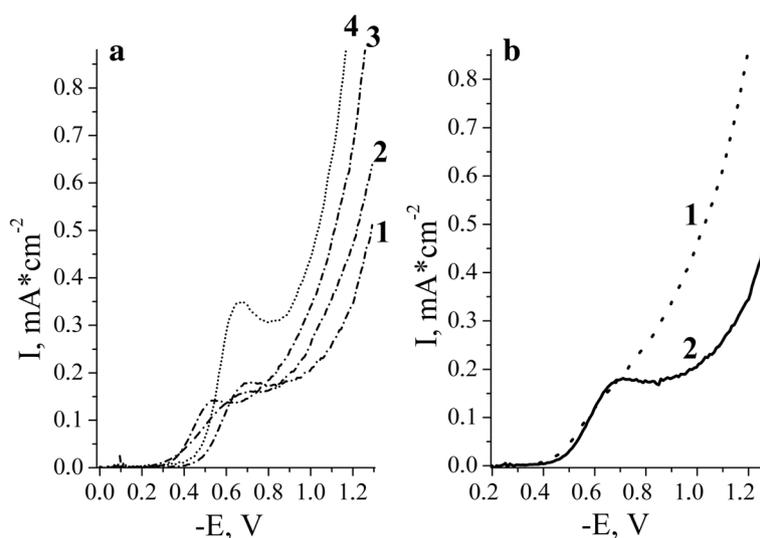


Fig. 5 **a** Current-voltage curves for oxygen reduction in solution of 0.9% NaCl at the electrodes: (1)— TiO_2 , (2)— $\text{TiO}_2/\text{Ni}^{2+}$, (3)— $\text{TiO}_2/\text{Co}^{2+}$, (4)— $\text{TiO}_2/\text{Cu}^{2+}$ (1% of dopant). **b** Current-voltage curves for oxygen reduction in solution of 0.9% NaCl at the $\text{TiO}_2/\text{Mn}^{3+}$ electrode: (1)—first cycle, (2)—after cycling; $v = 10 \text{ mV s}^{-1}$

Table 2 First order rate constants ($k' \times 10^5, s^{-1}$) Cr(VI) to Cr(III) ions photoreduction in the presence of TiO₂ and Mⁿ⁺/TiO₂ (M—Co, Ni, Mn, Cu) films with different dopant concentrations

Sample	Concentration of dopant ions				
	0%	1%	3%	5%	7%
	First order rate constants ($k' \times 10^5, s^{-1}$)				
Co/TiO ₂	3.3	4.4	4.1	4.4	3.8
Ni/TiO ₂		4.6	4.7	5.2	3.8
Mn/TiO ₂		4.5	4.2	3.5	3.6
Cu/TiO ₂		5.8	6.3	6.7	5.8

All doped films showed growth of photocatalytic activity compared with pure TiO₂. The optimum dopant ion concentration is 1% for Co²⁺ and Mn³⁺; 5% for Cu²⁺ and Ni²⁺. Creating the additional energy levels in the bandgap of semiconductor, dopant ions increase the time of recombination of photogenerated electrons and holes from the conduction and valence band of the TiO₂ and increase the efficiency of charge separation.

Conclusions

Nanostructured Mⁿ⁺/TiO₂ films having mesoporous structure with an average pore size of 2.5–6 nm and specific surface area from 147 (pure TiO₂) to 224 m²/g for manganese-containing samples were formed on glass and titanium substrates using template-assisted sol-gel method. After calcinations at 400 °C in the XRD patterns of annealed TiO₂ films doped with nickel or cobalt ions, only anatase nanocrystalline phase (8–20 nm) was observed; incorporation of 5% manganese or copper ions into TiO₂ structure lead to the formation of rutile phase. The enhancement of photocurrent efficiency of metal-doped electrodes in comparison with undoped TiO₂ indicates that Mⁿ⁺ ion addition is beneficial to promote charge separation within mesoporous TiO₂ film and to improve interfacial charge transfer process. For TiO₂ films doped with transition metal ions, the E_g values decrease with the increase of dopant content associated with the formation of new phases. Increase in Mⁿ⁺ content leads to the cathodic shift of the bottom of conduction band along with E_g decrease. Mⁿ⁺/TiO₂ (1%M—Co, Ni, Mn, Cu) electrodes with low dopant content possess high efficiency in electrocatalytic reduction of dissolved oxygen. Polarization curves of TiO₂, TiO₂/Ni²⁺, TiO₂/Co^{2+/3+}, and TiO₂/Mn³⁺ electrodes contain only one current wave current; it means that oxygen reduction proceeds without the formation of an intermediate product H₂O₂. The films containing 5 w/w % Cu, Mn, Ni, and Co exhibited the higher photoactivity in the processes of Cr(VI) to Cr(III) photoreduction comparing to

TiO₂ one. With increasing of dopant content, the decreasing of electrocatalytic activity and gradual decrease in the reaction rate constant of Cr(VI) to Cr(III) photoreduction for all 3d metals was observed. Synthesized covering can be used as effective photocatalysts and sensor elements.

Abbreviations

E_{cb}: Conductive band potential; E_{fb}: Flat band potential; E_g: Band gap; S_{BET}: Specific surface area; UV light: Ultraviolet light; XRD: X-ray diffraction

Authors' contributions

NS carried out the study and drafted the manuscript. IP was involved in the synthesis of the mesoporous films and the photocatalysis investigations. VV carried out electrochemical measurements. GK carried out investigation of oxygen electrocatalytic reduction. AE helped to draft the manuscript and participated in the design and coordination of the study. All authors read and approved the final manuscript.

Competing interests

The authors declare that they have no competing interests.

Publisher's Note

Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Author details

¹O.Chuiko Institute of Surface Chemistry, Ukrainian National Academy of Sciences, 17 General Naumov Street, Kyiv 03680, Ukraine. ²Institute of General & Inorganic Chemistry of National Academy of Sciences of Ukraine 32/34 Acad, Palladin Street, Kyiv 03680, Ukraine.

Received: 27 December 2016 Accepted: 14 March 2017

Published online: 31 March 2017

References

- Aroutiounian VM, Arakelyan VM, Shahnazaryan GE (2005) Metal oxide photoelectrodes for hydrogen generation using solar radiation-driven water splitting. *Sol Energy* 78:581–592
- Grätzel M (2007) Photovoltaic and photoelectrochemical conversion of solar energy. *Philosophical Trans Royal Soc A* 365(1853):993–1005
- Bahnmann DW, Koluiskaya SN, Dillert R et al (2002) Photodestruction of dichloroacetic acid catalyzed by nano-sized TiO₂ particles. *Appl Catalysis B: Environ* 36:161–169
- Yao M, Chen J, Zhao C, Chen Y (2009) Photocatalytic activities of Ion doped TiO₂ thin films when prepared on different substrates. *Thin Solid Films* 517:5994–5999
- Kobasa IM, Mazurkevich YS, Zozulya NI (2004) Effect of photochemical and reductive activation of titanium dioxide on its catalytic properties in deposition of metallic copper. *Teoreticheskaya i Eksperimental'naya Khimiya* 40(2):110–115
- Chiang K, Amal R, Tran T (2002) Photocatalytic degradation of cyanide using titanium dioxide modified with copper oxide. *Adv Environ Res* 6:471–485
- Cai R, Kubota Y, Fujishima A (2003) Effect of copper ions on the formation of hydrogen peroxide from photocatalytic titanium dioxide particles. *J Catalysis* 219:214–218
- Gracia F, Holgado JP, Caballero A, Gonzalez-Elipe AR (2004) Structural, optical, and photoelectrochemical properties of Mⁿ⁺-TiO₂ model thin film photocatalysts. *J Phys Chem B* 108:17466–17476
- Zhang X, Li X, Wu J, Yang R, Tian L, Zhang Z (2009) Simple sol-gel route to synthesis of mesoporous TiO₂. *J Sol-Gel Sci Technol* 51:1–3
- Zhang W, Li R, He H (2012) Synthesis of mesoporous TiO₂-Al₂O₃ binary oxides photocatalyst by sol-gel method using PEG1000 as template. *Int J Photoenergy Article ID* 108175:1–20
- Eremenko G, Smirnova N, Petr I et al (2004) Synthesis and properties of porous nanostructured films active in the ecological photocatalysis. *Nanosystems Nanomaterials Nanotechnologies* 2(2):477–488 (in Ukrainian)
- Yu G, Eremenko A, Smirnova N, Ilyin V (2005) Design and photocatalytic activity of mesoporous TiO₂/ZrO₂ thin films. *J Ads Sci Technol* 23(6):497–508

13. Smirnova N, Yu G, Eremenko A, et al (2006) Photoelectrochemical characterization and photocatalytic properties of mesoporous TiO₂/ZrO₂ films. *Int J Photoenergy* 8:1–6
14. Krylova GV, Gnatyuk Yu I, Eremenko AM et al (2009) Ag nanoparticles deposited onto silica, titania and zirconia mesoporous films synthesized by sol-gel template method. *J Sol-Gel Sci Technol* 50:216–228
15. López R, Gómez R, Lianos ME (2009) Photophysical and photocatalytic properties of nanosized copper-doped titania sol-gel catalysts. *Catal Today* 148:103–108
16. Ghasemi S, Rahimnejad S, Rahman Setayesh S et al (2009) Transition metal ions effect on the properties and photocatalytic activity of nanocrystalline TiO₂ prepared in an ionic liquid. *J Hazard Mater* 172:1573–1578
17. Xu JP, Shi SB, Li L et al (2009) Effect of manganese ions concentration on the anatase–rutile phase transformation of TiO₂ films. *J Phys Chem Solids* 70:511–515
18. Rocquefelte X, Goubin F, Koo H-J et al (2004) Investigation of the origin of the empirical relationship between refractive index and density on the basis of first principles calculations for the refractive indices of various TiO₂ phases. *Inorg Chem* 43:2246–2251
19. Devi LG, Kottam N, Murthy BN, Kumar SG (2010) Enhanced photocatalytic activity of transition metal ions Mn²⁺, Ni²⁺ and Zn²⁺ doped polycrystalline titania for the degradation of Aniline Blue under UV/solar light. *J Mol Catal A Chem* 328:44–52
20. Dong YL, Won JL, Jae Sung S et al (2004) Electronic surface state of TiO₂ electrode doped with transition metals, studied with cluster model and DV-X_c method. *Comput Mater Sci* 30:383–388
21. Choi W, Termin A, Hoffmann MR (1994) The role of metal ion dopants in quantum-sized TiO₂: correlation between photoreactivity and charge carrier recombination dynamics. *J Phys Chem* 98:13669–13679
22. Oleksenko L, Lutsenko L (2004) Co-containing systems based on zeolites ZSM-5, erionite, Al₂O₃ and SiO₂ in CO oxidation. *Chem Phys Techn Surf* 10: 132–136, in Ukrainian
23. Kosova N, Devyatkina E, Anufrienko V et al (2002) Using of mechanical activation in the rechargeable lithium batteries creation. *Chem Sustainable Dev* 10:127–133, in Russian
24. Liver L (1987) Electronic spectroscopy of nonorganic compounds. Part 2, Eds. M. Mir, 443 p (in Russian).
25. Sutapa R, Dibyendu G (1992) Optical properties of Ni²⁺-doped silica and silicate gel monoliths. *J Non-Cryst Sol* 151:203–208
26. Sjoerd Kijlstra W, Poels EK, Blik A et al (1997) Characterization of Al₂O₃-supported manganese oxides by electron spin resonance and diffuse reflectance spectroscopy. *J Phys Chem B* 101:309–316
27. Bezmaternyh L, Pocoluiko A, Yerlykova E, Edelman I (2001) Optical absorbance of copper metaborate CuB₂O₄. *Solid State Physics* 43:297–298, in Russian
28. Umabayashi T, Yamaki T, Itoh H, Asai K (2002) Analysis of electronic structures of 3d transition metal-doped TiO₂ based on band calculations. *J Phys Chem Sol* 63:1909–1920
29. Linsebigler AL, Lu GQ, Yates JT (1995) Photocatalysis on TiO₂ surfaces: principles, mechanism and selected results. *Chem Rev* 95:735–758
30. Gurevich Yu, Pleskon Yu (1983) Photoelectrochemistry of the semiconductors Eds. M. Nauka, 312 p. (in Russian).
31. Kolbasov G, Gorodyskiy A (1993) Photoinduced charge-transfer processes in semiconductor-electrolyte systems. Eds. Kyiv. Naukova dumka, 192 p. (in Russian).
32. Hamilton J W J, Byrne J A, Mc Cullagh C, Dunlop P S M (2008) Electrochemical investigation of doped titanium dioxide. Eds. Hindawi Publishing Corporation. *International J of Photoenergy* – 2008; Article ID 631597: 1 – 8.
33. Sakthivel S, Kish H (2003) Photocatalytic and photoelectrochemical properties of nitrogen-doped titanium dioxide. *Chem Phys* 4:487–490
34. Grätzel M, Gilbert SE, Klemenz C, Scheel HJ (1996) Electrochemical and photoelectrochemical investigation of single-crystal anatase. *J Am Chem Soc* 118:6716–6723
35. Fetter K (1967) *Electrochemical kinetics*, Eds. M. Chemistry, 856.
36. Kolbasov G Ja, Vorobets V S, Korduban A M (2006) Electrodes on the base of nanodispersed titanium and wolfram oxides for the dissolved oxygen sensors. *Zhurn Prikl Chem* 79:605 – 610.
37. Colon G, Hidalgo VC, Navio JA (2001) Influence of carboxylic acid on the photocatalytic reduction of Cr(VI) using commercial TiO₂. *Langmuir* 17:7174–7177
38. Schrank SG, José HJ, Moreira RFP (2002) Simultaneous photocatalytic Cr(VI) reduction and dye oxidation in a TiO₂ slurry reactor. *J Photochem Photobiol A: Chemistry* 147:71–76

Submit your manuscript to a SpringerOpen® journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Immediate publication on acceptance
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► springeropen.com
